



On behalf of ACEA, JAMA, KAMA, EUROBAT and ILA

Comparative LCA of Lead and LFP Batteries for Automotive Applications

Client: International Lead Association
Title: Comparative Life Cycle Assessment of Batteries for Automotive Applications
Report version: V1.4
Report date: 05/12/2020
© 2020 Sphera. All rights reserved

On behalf of Sphera Solutions Inc. and its subsidiaries

Document prepared by

Viviana Carrillo Usbeck

VCarrilloUsbeck@sphera.com

Project Manager /
Senior Consultant

Marta Bonell

Consultant

Quality assurance by

Manfred Russ



Consulting Manager, QA

05.12.2020

Under the supervision of

Dr. Johannes Gediga

Principal Consultant

This report has been prepared by Sphera Solutions, Inc. ("Sphera") with reasonable skill and diligence within the terms and conditions of the contract between Sphera and the client. Sphera is not accountable to the client, or any others, with respect to any matters outside the scope agreed upon for this project.

Sphera disclaims all responsibility of any nature to any third parties to whom this report, or any part thereof, is made known. Any such, party relies on the report at its own risk. Interpretations, analyses, or statements of any kind made by a third party and based on this report are beyond Sphera's responsibility.

If you have any suggestions, complaints, or any other feedback, please contact us at servicequality@sphera.com

Table of Contents

Table of Contents	3
List of Figures	6
List of Tables.....	7
List of Acronyms	9
Glossary	10
Executive Summary	12
1. Goal of the Study	14
2. Scope of the Study.....	15
2.1. Product System(s).....	15
2.2. Product Function(s) and Functional Unit	20
2.3. System Boundary	21
2.3.1. Time Coverage	22
2.3.2. Technology Coverage	22
2.3.3. Geographical Coverage	22
2.4. Allocation	23
2.4.1. Multi-output Allocation	23
2.4.2. End-of-Life Allocation	23
2.5. Cut-off Criteria	25
2.6. Selection of LCIA Methodology and Impact Categories	25
2.7. Interpretation to Be Used	28
2.8. Sensitivity and Scenario Analysis.....	28
2.9. Data Quality Requirements	29
2.10. Type and format of the report	29
2.11. Software and Database	30
2.12. Critical Review	30
3. Life Cycle Inventory Analysis	31
3.1. Data Collection Procedure.....	31
3.1.1. Lead Battery	31
3.1.2. LFP Battery	31
3.2. Production Stage.....	31

3.2.1.	Lead Battery	31
3.2.2.	LFP battery.....	33
3.3.	Use stage.....	34
3.4.	End of Life Stage	36
3.4.1.	LFP batteries EoL	36
3.4.2.	Lead-based batteries EoL	38
3.5.	Background Data	38
3.5.1.	Fuels and Energy	38
3.5.2.	Raw Materials and Processes	39
3.5.3.	Transportation	41
3.6.	Life Cycle Inventory Analysis Results	42
4.	Life Cycle Impact Assessment	47
4.1.	Overall Results Summary	47
4.2.	Primary Energy Demand	47
4.3.	Global Warming Potential	49
4.4.	Acidification Potential	51
4.5.	Eutrophication Potential	53
4.6.	Photochemical Ozone Creation Potential	55
5.	Interpretation	58
5.1.	Identification of Relevant Findings	58
5.2.	Assumptions and Limitations	60
5.3.	Sensitivity Analysis Results	60
5.3.1.	LFP battery weight reduction	61
5.3.2.	LFP battery lifetime increase	62
5.3.3.	Energy/fuel savings increase for LiB - LFP	63
5.3.4.	Vehicle lifetime increase.....	64
5.3.5.	EoL approach scenario	65
5.4.	LFP End of Life Scenario Analysis	67
5.5.	Data Quality Assessment.....	71
5.5.1.	Precision and Completeness	71
5.5.2.	Consistency and Reproducibility	71
5.5.3.	Representativeness	72
5.6.	Model Completeness and Consistency.....	72
5.6.1.	Completeness.....	72
5.6.2.	Consistency.....	72

5.7.	Conclusions, Limitations, and Recommendations.....	72
5.7.1.	Conclusions	72
5.7.2.	Limitations and Recommendations	74
References.....		75
Annex A:	Critical Review Statement	77

List of Figures

Figure 1-1: Overall Life Cycle GWP per battery technology and type of vehicle application	13
Figure 2-1: System boundary	21
Figure 2-2: Schematic representations of the cut-off and substitution approaches	23
Figure 3-1: Lead batteries EoL – Material recycling (substitution approach).....	38
Figure 4-1: Overall Life Cycle PED per battery technology, vehicle application and FU	48
Figure 4-2: Main contributors to the PED (manufacturing stage) per battery technology, vehicle application and FU	49
Figure 4-3: Overall Life Cycle GWP per battery technology, vehicle application and FU	50
Figure 4-4: Main contributors to the GWP (manufacturing stage) per battery technology, vehicle application and FU	51
Figure 4-5: Overall Life Cycle AP per battery technology, vehicle application and FU.....	52
Figure 4-6: Main contributors to the AP (manufacturing stage) per battery technology, vehicle application and FU	53
Figure 4-7: Overall Life Cycle EP per battery technology, vehicle application and FU.....	54
Figure 4-8: Main contributors to the EP (manufacturing stage) per battery technology, vehicle application and FU	55
Figure 4-9: Overall Life Cycle POCP per battery technology, vehicle application and FU	56
Figure 4-10: Main contributors to the POCP (manufacturing stage) per battery technology, vehicle application and FU	57
Figure 5-1: Sensitivity analysis – total GWP – LFP battery weight reduction	62
Figure 5-2: Sensitivity analysis – total GWP – LFP battery lifetime increase	63
Figure 5-3: Sensitivity analysis – GWP per LC stage for PbB and LiB - LFP for Start-stop and Micro-hybrid vehicles – 1% higher fuel saving for LiB - LFP battery	64
Figure 5-4: Sensitivity analysis – total GWP – vehicle lifetime increase.....	65
Figure 5-5: Sensitivity analysis – total GWP – EoL approach.....	66
Figure 5-6: LFP Battery Physical and Pyrometallurgical Processing	68
Figure 5-7: Lithium Carbonate and Metal Salt Production.....	69

List of Tables

Table 2-1: Automotive Batteries Technical Parameters	18
Table 2-2: Use stage total fuel saving per Functional Unit	19
Table 2-3: Battery reference flows per Functional Unit	20
Table 2-4: System boundaries	22
Table 2-5: Impact category descriptions.....	27
Table 2-6: Other environmental indicators	28
Table 3-1: Average gate-to-gate data for one production volume average Lead batteries	32
Table 3-2: Bill of Material and production data for one LFP battery.....	33
Table 3-3: Additional fuel consumption due to battery weight difference	36
Table 3-4: Combustion emission factors 1 kg gasoline consumed (passenger car)	36
Table 3-5: End of Life Cycle – LFP battery	37
Table 3-6: Key energy datasets used in inventory analysis	38
Table 3-7: Key material and process datasets used in inventory analysis for Lead Battery	39
Table 3-8: Key material and process datasets used in inventory analysis for LFP Battery	40
Table 3-9: Transportation and road fuel datasets.....	41
Table 3-10: Use stage vehicle datasets.....	41
Table 3-11: LCI results of total battery life cycle per battery type and FU – Conventional ICE application (units in kg unless otherwise noted)	42
Table 3-12: LCI results of total battery life cycle per battery type and FU – Start-Stop application (units in kg unless otherwise noted).....	43
Table 3-13: LCI results of total battery life cycle per battery type and FU – Micro-hybrid application (units in kg unless otherwise noted)	45
Table 4-1: Total Life Cycle LCIA for Lead and LFP batteries per vehicle application and FU	47
Table 4-2: Primary energy demand from ren. and non ren. Resources (PED) [MJ]	48
Table 4-3: Global Warming Potential [kg CO ₂ eq.].....	50
Table 4-4: Acidification Potential [kg SO ₂ eq.].....	52
Table 4-5: Eutrophication Potential (EP) [kg Phosphate eq.]	54
Table 4-6: Photochemical Ozone Creation Potential (POCP) [kg Ethene eq.].....	56
Table 5-1: Summary of results main contributors for all battery types, vehicle applications and FU in percentage	58
Table 5-2: Battery reference flows per Functional Unit (LFP battery weight reduction).....	61
Table 5-3: Global Warming Potential [kg CO ₂ eq.] – LFP weight sensitivity	61
Table 5-4: Battery reference flows per Functional Unit (LFP battery lifetime increase)	62
Table 5-5: Global Warming Potential [kg CO ₂ eq.] – LFP lifetime sensitivity – scenario A	62
Table 5-6: Global Warming Potential [kg CO ₂ eq.] – LFP lifetime sensitivity – scenario B.....	63
Table 5-7: Global Warming Potential [kg CO ₂ eq.] –1% fuel savings sensitivity	63
Table 5-8: Battery reference flows per Functional Unit (vehicle lifetime increase)	64
Table 5-9: Global Warming Potential [kg CO ₂ eq.] – vehicle lifetime sensitivity	65

Table 5-10: Global Warming Potential [kg CO ₂ eq.] – EoL approach	66
Table 5-11: End of Life Cycle – LFP Battery Recovery Scenario Components Treatment.....	70
Table 5-12: End of Life Cycle – LFP Battery Recovery Scenario Results	70

List of Acronyms

ADP	Abiotic Depletion Potential
AGM	Absorbent Glass Mat
AP	Acidification Potential
BOM	Bill of Materials
CML	Centre of Environmental Science at Leiden
EAF/SAF	Electric Arc Furnace / Submerged Arc Furnaces
EF	Environmental Footprint
ELCD	European Life Cycle Database
EoL	End-of-Life
EP	Eutrophication Potential
EFB	Enhanced Flooded Battery
FU	Functional Unit
GaBi	Ganzheitliche Bilanzierung (German for holistic balancing) - LCA software
GHG	Greenhouse Gas
GWP	Global Warming Potential
ILCD	International Reference Life Cycle Data System
ICE	Internal Combustion Engine
ISO	International Organization for Standardization
ISS	Idle Stop Start
LCI / LCIA	Life Cycle Inventory / Life Cycle Assessment
LCIA	Life Cycle Impact Assessment
LiB	Lithium ion Battery
LFP	Lithium Iron Phosphate
MPV	Multi-Purpose Vehicles
NMVOC	Non-Methane Volatile Organic Compound
PbB	Lead battery / Lead-based battery
PED	Primary Energy Demand
PEFCR	Product Environmental Footprint Category Rules
POCP	Photochemical Ozone Creation Potential
SLI	Starting, Lighting, and Ignition
VRLA	Valve Regulated Lead Acid Battery
VOC	Volatile Organic Compound

Glossary

Life cycle

A view of a product system as “consecutive and interlinked stages ... from raw material acquisition or generation from natural resources to final disposal” (ISO 14040:2006, section 3.1). This includes all material and energy inputs as well as emissions to air, land and water.

Life Cycle Assessment (LCA)

“Compilation and evaluation of the inputs, outputs and the potential environmental impacts of a product system throughout its life cycle” (ISO 14040:2006, section 3.2)

Life Cycle Inventory (LCI)

“Phase of life cycle assessment involving the compilation and quantification of inputs and outputs for a product throughout its life cycle” (ISO 14040:2006, section 3.3)

Life Cycle Impact Assessment (LCIA)

“Phase of life cycle assessment aimed at understanding and evaluating the magnitude and significance of the potential environmental impacts for a product system throughout the life cycle of the product” (ISO 14040:2006, section 3.4)

Life cycle interpretation

“Phase of life cycle assessment in which the findings of either the inventory analysis or the impact assessment, or both, are evaluated in relation to the defined goal and scope in order to reach conclusions and recommendations” (ISO 14040:2006, section 3.5)

Functional unit

“Quantified performance of a product system for use as a reference unit” (ISO 14040:2006, section 3.20)

Allocation

“Partitioning the input or output flows of a process or a product system between the product system under study and one or more other product systems” (ISO 14040:2006, section 3.1 7)

Closed-loop and open-loop allocation of recycled material

“An open-loop allocation procedure applies to open-loop product systems where the material is recycled into other product systems and the material undergoes a change to its inherent properties.”

“A closed-loop allocation procedure applies to closed-loop product systems. It also applies to open-loop product systems where no changes occur in the inherent properties of the recycled material. In such cases, the need for allocation is avoided since the use of secondary material displaces the use of virgin (primary) materials.”

(ISO 14044:2006, section 4.3.4.3.3)

Foreground system

“Those processes of the system that are specific to it ... and/or directly affected by decisions analysed in the study.” (JRC, 2010, p. 97) This typically includes first-tier suppliers, the manufacturer itself, and any downstream life cycle stages where the manufacturer can exert significant influence. As a general rule, specific (primary) data should be used for the foreground system.

Background system

“Those processes, where due to the averaging effect across the suppliers, a homogenous market with average (or equivalent, generic data) can be assumed to appropriately represent the respective process ... and/or those processes that are operated as part of the system but that are not under the direct control or decisive influence of the producer of the good.... ” (JRC, 2010, pp. 97-98) As a general rule, secondary data are appropriate for the background system, particularly where primary data are difficult to collect.

Critical Review

“Process intended to ensure consistency between a life cycle assessment and the principles and requirements of the International Standards on life cycle assessment” (ISO 14044:2006, section 3.45).

Proxy data

Data used to study a situation, phenomenon or condition for which no direct information - such as instrumental measurements - is available.

Executive Summary

Goal of the Study

The goal of the study is to assess the comparative life cycle environmental profile of two different battery chemistries used in the automotive sector. This study assesses the cradle-to-grave environmental impact of lead-based battery compared to an LFP automotive battery within Europe. The study is conducted according to ISO 14040/44, the international standards on life cycle assessment (LCA).

Application / audience

The results of the study are to be used by the Manufacturers Association (ACEA), Japan Automobile Manufacturers Association (JAMA), Korea Automobile Manufacturers Association (KAMA), Association of European Automotive and Industrial Battery Manufacturers (EUROBAT), and the International Lead Association (ILA), to improve their understanding of the environmental impact of lead-based battery production from cradle-to-grave and promote continuous improvement in the environmental sustainability of lead batteries. The data generated from the study will help ACEA, JAMA, KAMA, EUROBAT, and ILA to respond to demands from various stakeholders for reliable, quantified environmental data. Finally, the study enables ACEA, JAMA, KAMA, EUROBAT to continue to participate in and contribute to a range of sustainability initiatives and the ongoing methodological discussions within LCA and related disciplines.

The intended audience for this study includes ACEA, JAMA, KAMA, EUROBAT, and the ILA lead and battery producers, legislators, customers, environmental practitioners, and non-governmental organizations.

Critical Review

A third-party critical review panel of the study according to ISO 14040, ISO 14044, and ISO/TS 14071 is carried out by Matthias Finkbeiner from Technical University Berlin, Jeffrey Spangenberg, and Qiang Dai from Argonne National Lab (ANL), and Eberhard Meissner, Battery specialist.

Main findings

The batteries assessed in this study are required in conventional, start-stop, and micro-hybrid vehicles. Based on the assumptions defined for the study, the use stage dominates the overall life cycle for all battery types (Pb and LFP) for start-stop and micro-hybrid due to the fuel-saving. The lead batteries have a higher weight compared to the LFP batteries, which leads to an increase in fuel consumption. This effect is particularly significant for the conventional batteries. Figure 1-1 displays the overall GWP per battery technology and type.

In the manufacturing stage for PbB, lead production and electricity use are most often the primary drivers of impacts. Raw materials like sulfuric acid and plastic parts can also have a noticeable contribution. For LFP batteries, cell raw materials and electronics have a higher contribution to the manufacturing stage, while crash protection and car cabling have minor contributions to all impact categories analysed. Under the baseline scenario described in Table 2-3, the environmental impacts of manufacturing the LFP battery compared to manufacturing the lead-based battery are roughly greater by a factor of 6.

In EoL, the collection rate is 97.3% for all battery types and applications (based on an analysis of collection rates seen for automotive lead batteries in the EU). After disassembly, the substitution approach has been applied for PbB where these batteries are recycled and are used in the production of secondary lead on the input side of the production stage. LFP batteries are disassembled into separate components that are treated separately; cells are sent to incineration with energy recovery and all other materials such as

battery casings, cabling and electronics are sent to material recovery with the application of credits accordingly.

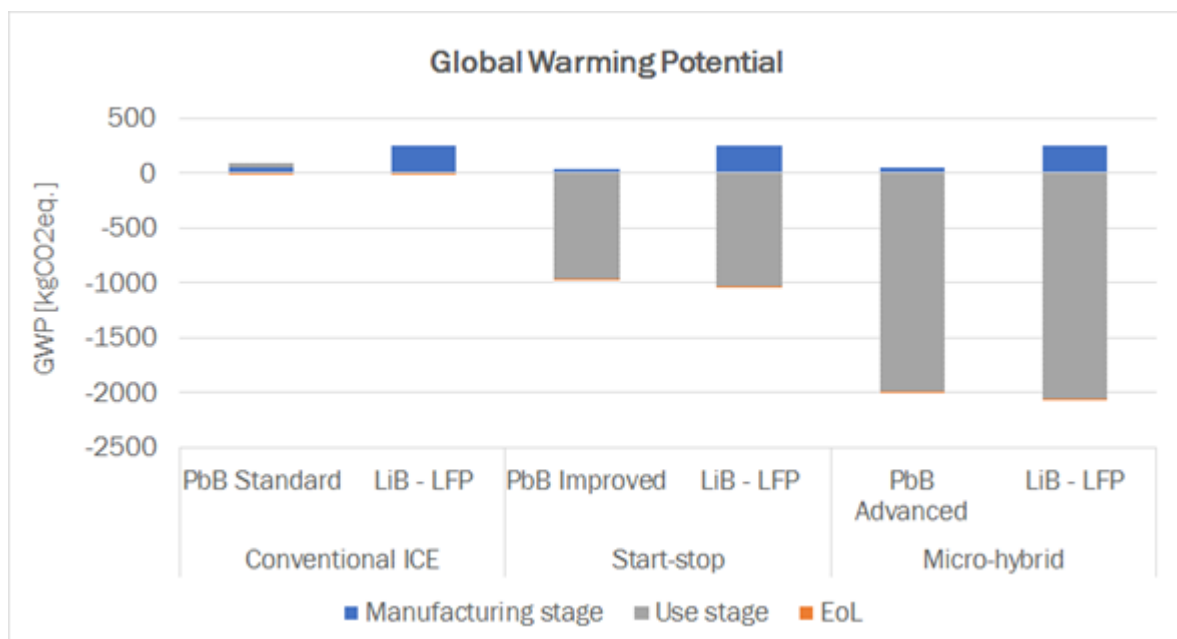


Figure 1-1: Overall Life Cycle GWP per battery technology and type of vehicle application

Conclusions and recommendations

The results of this study are only applicable to lead and LFP batteries used for the described automotive applications in Europe. Even in this case, the lack of primary data for LFP as well as assumptions regarding battery weights, composition, and performance, have to be reflected when interpreting the representativity of the results.

It may not be appropriate to extrapolate these results to other regions, especially if there are significant differences in lead-based battery recycling rates, energy grid mixes, etc. In addition, LFP is not representative of all lithium battery chemistries and the results for other types of Li-ion batteries could be significantly different.

This study shows that:

- Start-stop and micro hybrid vehicles offer substantial life cycle benefits compared to conventional ICE vehicles;
- lower battery weight and higher lifespan is recommended to reduce the impacts of battery manufacturing and maximise in use benefits;
- increasing material-based recycling of LFP is recommended to reduce reliance on virgin raw materials.

It is recommended to:

- Study Lithium ion battery types comprising cathode materials other than LFP;
- More specifically study the use phase impacts of batteries;
- Study LiB – LFP with primary industry data rather than relying on secondary information from the available literature.

1. Goal of the Study

The goal of the study is to assess the comparative life cycle environmental profile of two different battery chemistries used in the automotive sector. This study assesses the cradle-to-grave environmental impacts of a lead-based battery compared to an LFP automotive battery within Europe. The study is conducted according to ISO 14040/44, the international standards on life cycle assessment (LCA).

The results of the study are to be used by the Manufacturers Association (ACEA), Japan Automobile Manufacturers Association (JAMA), Korea Automobile Manufacturers Association (KAMA), Association of European Automotive and Industrial Battery Manufacturers (EUROBAT), and the International Lead Association (ILA), to improve their understanding of the environmental impact of lead-based battery production from cradle-to-grave and promote continuous improvement in the environmental sustainability of lead batteries. The data generated from the study will help ACEA, JAMA, KAMA, EUROBAT, and ILA to respond to demands from various stakeholders for reliable, quantified environmental data. Finally, the study enables ACEA, JAMA, KAMA, EUROBAT to continue to participate in and contribute to a range of sustainability initiatives and the ongoing methodological discussions within LCA and related disciplines.

The intended audience for this study includes ACEA, JAMA, KAMA, EUROBAT, and the ILA lead and battery producers, legislators, customers, environmental practitioners and non-governmental organizations.

A third-party critical review panel of the study according to ISO 14040, ISO 14044 and ISO/TS 14071 is carried out by Matthias Finkbeiner from Technical University Berlin¹, Jeffrey Spangenberg and Qiang Dai from Argonne National Lab (ANL), and Eberhard Meissner, Battery specialist. The final review statement is documented in Annex A.

This technical report will be publicly available and can be made accessible to interested parties upon request to the study commissioners (ACEA, JAMA, KAMA, EUROBAT, and the ILA). The study commissioners may use the study report to prepare and provide information materials, for example, a technical summary of the report, a flyer addressing the major outcomes of the study and other materials.

The results of the study are intended to be used e.g. for comparative assessments intended to be disclosed to the public. It is acknowledged that the data provided might be used by others for further comparative assessments. Such comparisons should only be made on a product system basis and be carried out in accordance with the ISO 14040/44 standards, including an additional critical review by a panel (ISO 14040:2006 and ISO 14044:2006).

¹ The reviewer acts and was contracted as an independent expert, not as a representative of his affiliated organization.

2. Scope of the Study

The following sections describe the general scope of the project to achieve the stated goals. This includes, but is not limited to, the identification of specific product systems to be assessed, the product function(s), functional unit and reference flows, the system boundary, allocation procedures, and cut-off criteria of the study.

2.1. Product System(s)

The document assesses three type of vehicle systems: conventional combustion engines (ICE), start-stop, and micro-hybrid. Three different types of lead batteries are assessed for these applications (standard, EFB and AGM). EFB and AGM are more suitable to the vehicle requirements in start-stop and micro-hybrid applications. One type of lithium-ion battery is assessed for the three vehicle system types. This is a lithium iron phosphate battery (LiB – LFP), which can be used in all three vehicle system types. The following paragraphs describe the batteries more in detail and the data used in this study can be found in the LCI section 3 of the present report.

Lead-based batteries applied to vehicles

Lead batteries are long-established for automotive applications, they are used to start the engine and to provide energy if other power sources become unavailable. The technical requirements for automotive service have become more onerous in the last few years as car manufacturers have adapted vehicle powertrains to reduce emissions. This has required batteries to be able to provide multiple engine starts and recover energy in operation for stop and start or micro-hybrid service. Lead batteries have been successfully developed to provide reliable performance for these conditions. (Ricardo, 2020)

Battery life has been improved and better manufacturing technology has resulted in greater efficiencies both in production and materials used. Lead batteries are also very effectively recycled at end-of-life. Lead is the most efficiently recycled commodity metal and lead batteries are the only battery system that is almost completely recycled, with over 97.3% of lead batteries being collected and recycled in Europe (IHS Markit, 2019).

Lead batteries all share the same basic chemistry. The active materials are lead and lead dioxide and the electrolyte is an aqueous solution of dilute sulfuric acid. The active materials both react with sulfuric acid on discharge to form lead sulphate. The current collectors are lead or lead alloys and the battery containers are moulded polymers. The positive and negative plates are separated by microporous plastic or microfibre glass separators. Lead batteries may be flooded with free electrolytes with vents that allow passage of gas to and from the cells. At top of charge, flooded lead batteries evolve some hydrogen and oxygen from the electrolysis of water.

This is minimised in modern automotive batteries by the design of the battery such that water loss is not a failure mode in normal service. Positive grid corrosion may occur but lead alloy selection ensures this is at a rate that permits a full-service life. Lead batteries may also be valve-regulated lead-acid (VRLA) variants that are sealed in operation and where water loss is reduced by internal recombination of oxygen gas. These types have a one-way valve to allow small quantities of hydrogen to be vented but do not permit air to enter the cells. Two types are used: one has absorptive glass mat (AGM) separators with the electrolyte immobilised in the active materials and the separator; the other has microporous polymeric separators with the electrolyte gelled with fine silica powder and the remainder immobilised in the active materials.

All VRLA batteries operate in the same way with oxygen generated at the positive plate at top of charge diffusing through connected porosity in the separator to be chemically recombined at the negative plate. In this way, water loss is reduced to very low levels. Hydrogen evolution is minimised by careful materials selection which also limits positive grid corrosion. VRLA AGM batteries are widely used in automotive and industrial applications but VRLA gel batteries are principally used for industrial applications.

Lithium batteries applied to vehicles

Li-ion batteries share several common features but there is wide variation in the active materials used. The electrolyte is a solution of lithium salt in an organic solvent mixture. The dissociating salt provides ionic conductivity to the electrolyte. The positive electrode active material is a lithium compound coated onto aluminium foil and the negative electrode material coats a copper foil. The separator is a thin microporous polymer membrane. Cells may be in cylindrical cans, prismatic metal cans, or in aluminised polymer foil pouches.

The lithium compounds used as positive active materials may be lithium cobalt oxide (LCO), lithium nickel-cobalt-manganese oxide (NMC), lithium nickel-cobalt-aluminium oxide (NCA), lithium manganese oxide (LMO), or lithium iron phosphate (LFP). The positive active materials can reversibly release and store lithium, which enters the electrolyte undergoing charge-transfer reactions, to pass as Li^+ ions to the negative electrode. Corresponding to the positive active material, the negative active material is able for reversible acceptance, storage, and release of lithium (intercalation). Materials used are carbon, graphite, silicon, lithium titanate (LTO), and mixtures thereof.

Automotive batteries applications

The following automotive batteries applications are assessed in this study:

- **Conventional ICE;** batteries are used in the vast majority of most conventional vehicles to provide starter, lighting, and ignition (SLI) functions.
- **Start-stop** - batteries are used in vehicles with an idle start-stop (ISS) system, which allows the ICE to automatically shut down under braking and rest and then to restart.
- **Micro-hybrid** - batteries used in vehicles with a micro-hybrid system, which combines start-stop functionality with regenerative braking (a system to recover and restore energy from braking), and other micro-hybrid features. This type of duty requires higher resilience of the battery with deep-cycling and a high rate of charge acceptance.

For these 3 different automotive battery applications, a comparison is made between different lead batteries (PbB) vs. lithium iron phosphate batteries (LFP). The following battery technologies are analysed:

- **Lead (Pb) 12 V, 70 Ah**
 - Standard Technology - flooded lead-based batteries are used as standard technology batteries in the majority of conventional vehicles. Flooded lead-based batteries are characterized by a vented design and an excess of free-flowing aqueous electrolyte between and above the electrode stack.
 - Improved Technology-enhanced flooded (EFB) or Absorbent Glass Matt (AGM) lead-based batteries used in vehicles with a start-stop system.
 - Advanced Technology - EFB or AGM lead-based batteries are used in vehicles with a micro-hybrid system.
- **Li-ion (LFP) 12 V, 60 Ah** – it is assumed that LFP battery cells are used for all three applications.

12 V lead batteries for automotive service are supplied in three types; conventional SLI (starting, lighting and ignition), EFB (enhanced flooded batteries), and AGM (absorptive glass mat). SLI batteries are used for vehicles without stop and start/idle stop-start/micro-hybrid system. They provide one cold engine start per journey and reserve power as required. EFB and AGM batteries are used for vehicles with stop and

start systems. In addition to cranking the cold engine and providing reserve power, in these applications they have the capability of multiple warm engine starts so that the engine may be stopped when the vehicle is stationary and restarted automatically when the vehicle moves off to reduce emissions and improve fuel economy. They are not fully charged in operation so that the battery can accept charge for energy recovery as well as provide power on discharge to supply vehicle systems when the engine is stopped. For the purposes of this study, EFB and AGM batteries are regarded as equivalent although AGM types are generally regarded as technically superior.

EFB batteries differ from SLI batteries in that they retain a flooded construction with free electrolyte while SLI batteries have inactive material formulation, active material retention, the use of additives in the negative plates, and have an electrochemical design. AGM batteries use special separators which immobilise the electrolyte and permit the battery to operate in a fully sealed manner such that any oxygen evolved in operation is chemically recombined and hydrogen loss is suppressed by the electrochemical design. This construction provides higher cycle life in stop and start systems so that for more arduous service, AGM batteries are preferred.

Within this study, for all 3 different types of applications, conventional, start-stop and micro-hybrid, the same design of 12 V LFP battery is considered – other than the lead battery, which has different designs specific to each application. Lithium ion batteries can be used for vehicles with or without stop and start systems. If the vehicle has a stop and start system, it will operate in a partially discharged condition like an EFB or an AGM battery for the same reason. If the vehicle has no stop and start capability, it can be fully charged in the same manner as a lead-type SLI battery. Li-ion batteries for 12 V service generally use lithium iron phosphate (LFP) cathodes rather than nickel-manganese-cobalt (NMC) cathodes because their cell voltage (3.2 V per cell) allows for a good match to the vehicles electrical system voltage of ~15V max when combined with carbon as a negative material (4 cells in series). Other combinations of positive and negative active materials are less appropriate (e. g. NMC vs. C with 3.7 V per cell).

The functional unit in the study is “Rechargeable storage of energy to fulfil the service lifetime of a vehicle”. A lead battery of 70 Ah is utilized in these applications. The current lithium-ion offering on the market which meets the functional unit is an LFP battery of 60 Ah. (Ricardo, 2020) (A123 Systems, 2020). Hence these two technologies have been compared in the document.

Automotive Batteries Use Stage

The following Table 2-1 provides the main technical parameters per battery type and technology. Table 2-2 shows the total fuel saving per year considered as baseline for the use stage modelling and calculation of results. (EPA, 2016)

The following parameters are representative of European weather conditions and light duty vehicles.

Table 2-1: Automotive Batteries Technical Parameters²

Application	Conventional ICE		Start-stop		Micro-hybrid	
Battery type	Pb Standard	Li-ion LFP	Pb Improved	Li-ion LFP	Pb Advanced	Li-ion LFP
Battery nominal capacity	70 Ah	60 Ah	70 Ah	60 Ah	70 Ah	60 Ah
Cold starts per day	3					
Cold starts per year	1000					
Vehicle life	10 years					
Cold engine start	3 kW for 3 s, 2.5 kWh per year					
Warm starts per day	None		15			
Warm starts per year	None		5000			
Warm engine cranking events	-		2 kW for 0.5 s = 1.4 kWh per year			
Additional duty	-		25 h in stop phase at 0.24 kW = 6.0 kWh		1.5 kW of battery ancillary loads, 25% of operating time (75 h) = 112 kWh	
Battery discharge	50% SoC 5 times per year, 420 Wh x 5 = 2.1 kWh (35 Ah for PbA but LFP discharged to 42% SoC if 60 Ah nominal capacity)					
Vehicle drives	15,000 km per year, average speed 50 kph, operates 300 h per year, 100 h city driving, 200 h highway driving					
Top-of-charge current	3 mA/Ah at top of charge	Shuts down at top of charge, no	Maintained at 80-85% SoC in normal operation with a narrow range of SoC above and below set point, never reaches top of charge			

² Geoffrey May Focus Consulting 2020 and; ACEA, JAMA, KAMA Survey 2020, Ricardo (2020) Lead Battery Automotive Trends Review-Final Report RD19-001611-11, A123 UltraPhosphate Lithium Ion 12v starter battery specifications downloaded from <http://www.a123systems.com/automotive/products/systems/12v-starter-battery/> on 18/6/2020, Previous ELV Annex II (2014) submissions on lithium ion starter batteries by Contribution of A123 Systems, Fraunhofer, LG Chem and Samsung SDI.

		overcharge current				
Self-discharge (at 25 °C per month)	2.5% = 21 Ah per year	1% = 7.2 Ah per year	2.5% = 21 Ah per year	1% = 7.2 Ah per year	2.5% = 21 Ah per year	1% = 7.2 Ah per year
Charging efficiency	90%	95%	90%	95%	90%	95%

For start-stop and micro-hybrid with EFB or AGM batteries, the baseline duty cycle is the same as SLI batteries. There is one cold start per journey. The vehicle is used for 300 h per year and it has 50% discharges per year; same goes over a 10-year life. The difference is that in city driving, the ISS system operates, and 100 h of city driving are assumed.

The battery is operated in a partial state-of-charge (PSoc) of 80-85% such that it can always accept charge and can provide power when required. It will not reach top of charge.

More information regarding the fuel saving approach choice is available under section 3.3.

Table 2-2: Use stage total fuel saving per Functional Unit

Application	Conventional ICE ³		Start-stop		Micro-hybrid	
Battery type	Pb Standard	Li-ion LFP	Pb Improved	Li-ion LFP	Pb Advanced	Li-ion LFP
Gasoline consumption (litre/100 km)	5.10		4.90		4.69	
Percentage of fuel saving (%)	-		4% ⁴		8% ⁵	
Fuel saving (Litre / total vehicle lifetime)	0		-306		-612	

It has been assumed that in vehicles currently available on the market, the energy/fuel savings for lead batteries and LFP batteries in start-stop and micro-hybrid vehicles are similar. This is because existing energy management systems are not able to realize the full potential of enhanced charge acceptance seen in LFP batteries. This assumption is based on an ACEA survey of members where 75% of respondents reported that the CO₂ savings in the use phase of micro-hybrids would be of the same magnitude when using a lead or LFP battery. However, given some companies reported there may be up to a 1% difference in favour of LFP, a sensitivity assessment of this has been undertaken in section 5.3. (ACEA, 2020)

³ Derived from average fuel consumption values for MPV from www.fuelmileage.co.uk

⁴ EPA, Proposed Determination on the Appropriateness of the Model Year 2022-2025 Light-Duty Vehicle Greenhouse Gas Emissions Standards under the Midterm Evaluation: Technical Support Document (3 - 5%)

⁵ EPA, Proposed Determination on the Appropriateness of the Model Year 2022-2025 Light-Duty Vehicle Greenhouse Gas Emissions Standards under the Midterm Evaluation: Technical Support Document (7 - 9. 5%)

2.2. Product Function(s) and Functional Unit

The rechargeable batteries considered in this study are designed to store energy for automotive purposes and to deliver energy to the applications as required.

Rechargeable batteries for all applications must provide power measured in kW for the required time to deliver energy (kWh) for the intended application. The energy storage capacity is measured in kWh which is the nominal capacity of the battery and the total energy provided over the service life of the battery; it is also measured in kWh over the total of charge and discharge cycles. This may also be referred to as capacity turnovers.

The energy consumption in actual use is the total energy delivered to the application load plus self-discharge, the overcharge current, and charging efficiency as a result of resistive heating losses. In the case of LFP batteries, although there is no current flowing through the cells, the battery management circuitry will consume a very small current which will be additive to the self-discharge.

The functional unit is:

Rechargeable storage of energy to fulfil the service lifetime of a vehicle (10 years / 150,000 km)

Table 2-3: Battery reference flows per Functional Unit

Lead battery type / application	Weight (kg)	Capacity (Ah)	Life-time (years)	No. of batteries vehicle lifetime	Li-ion battery type	Weight (kg) ⁶	Capacity (Ah)	Life-time (years)	No. of batteries vehicle lifetime
Standard/Conventional ICE	18	70	5	2	LFP	12	60	8	1.25
Improved/Start-stop	19	70	5.5	1.82	LFP	12	60	8	1.25
Advanced/Micro-hybrid	20	70	6	1.66	LFP	12	60	8	1.25

Lead battery lifetime differs according to real world conditions (i.e. average temperature, usage patterns) and a single representative value does not exist. The average lifetime values used in this LCA report were calculated according to a confidential survey of EUROBAT's membership. The values were then discussed and validated as "representative" by EUROBAT's Automotive Battery Committee. (EUROBAT, 2020)

The lifetime of a battery also depends on various parameters including temperature, charging voltage, floating voltage and discharge cycles. It is assumed that all batteries operate under stable temperature conditions of 20 °C. It may be necessary to add heating or cooling devices to LFP batteries used in hot or cold territories depending on the location of the battery in the vehicle, but this is outside the scope of this study.

⁶ The LFP battery weight of 12 kg has been chosen as the baseline and representative of most 60 Ah LFP 12 V SLI batteries on the market based on available literature references. Some lighter LFP batteries of approximately 10 kg may be available and we have therefore conducted a sensitivity assessment at this weight (see section 2. 8)

The LFP battery weight indicated in Table 2-3 considers the weight of one battery with electronics. Additional components required in the vehicle such as crash protection and car cabling are also included in the assessment, but not included in the weight; their use is independent from the battery lifetime and does not influence the number of batteries needed to match the functional unit.

The lead-based batteries weight and production data represents the average inventory profiles from EUROBAT participating companies.

2.3. System Boundary

The system boundary of the study is cradle-to-grave. This includes raw material extraction and/or processing, inbound transport to the production facility, battery materials manufacturing, battery assembly, use stage of the battery over the lifetime of the vehicle and EoL treatment. Figure 2-1 presents all potential life cycle stages.

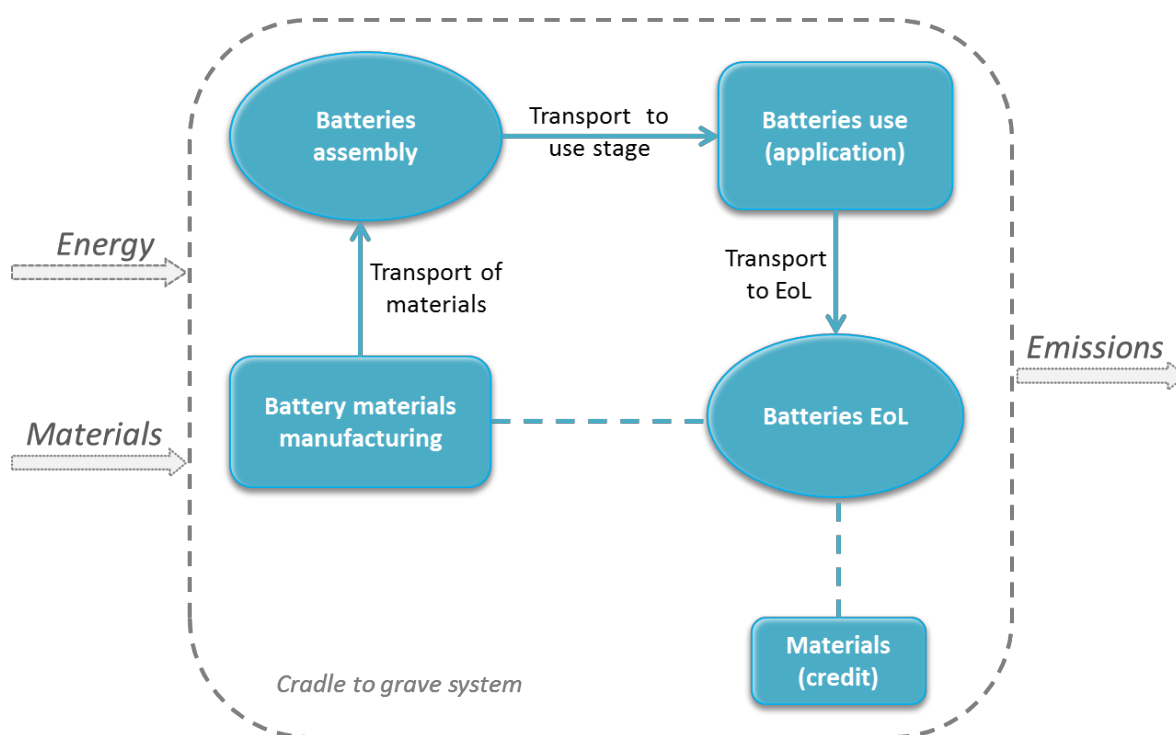


Figure 2-1: System boundary

Inclusions and exclusions to the system boundary are listed in Table 2-4

Table 2-4: System boundaries

Included	Excluded
✓ Extraction and processing of materials	✗ Production and maintenance of capital equipment and infrastructure
✓ Electronics and crash protection in the application (only for LFP battery)	✗ Overhead (heating, lighting, services) for manufacturing facilities
✓ Car cabling	✗ Labour
✓ All associated energy and fuels	✗ Packaging
✓ Transportation of raw and processed materials	✗ Production for the application (vehicles)
✓ Transport to customer	
✓ Use stage	
✓ End-of-life (collection, recycling, treatment)	

Electronics and crash protection are battery supporting components exclusively needed for LFP batteries and are not required for lead-based batteries. Car cabling has been considered for both battery types in the same way.

Packaging of raw materials and final product is excluded from the study as it is expected to have a minimal contribution to the total impact. Production and maintenance of capital goods are also excluded from the study. It is expected that these impacts are negligible compared to the impacts associated with running the equipment over its operational lifetime. (Sphera, 2020)

The EoL includes the collection of batteries and its treatment for the recovery of materials, please see section 2.4.2 for details on EoL approach.

2.3.1. Time Coverage

The results of this study are intended to represent the year 2017. They are relevant for 2019/20 (the year in which the study was conducted) and are expected to be relevant until such time as there is a significant change in the production mix, energy mix, or manufacturing technology.

2.3.2. Technology Coverage

This study assesses the cradle-to-grave impacts of lead-based and LFP batteries including the battery production, its use within an application (automotive), and their eventual EoL based on the current European technology mix. For the lead batteries, primary average data have been used from EUROBATs' European members to ensure that the model used to assess the environmental impact of lead is technologically representative for each stage of the production process. For LFP batteries literature data has been used and represents batteries used in European vehicles. Please see Table 3-6, to Table 3-9 for more information on the background data used.

2.3.3. Geographical Coverage

The results of this study are intended to represent lead battery produced in European countries (production and assembly in Europe) and LFP battery produced in Asian countries (mainly China for cell materials production and assembly of imported cells in Europe). The upstream data on energy and fuels are based on region.

For European production, regional EU-28 data is used where national data are unavailable. These data are combined with primary data gathered from manufacturing sites to ensure that the data and models are representative of the relevant region. The use and EoL stages of the life cycle for all battery types are assumed to be in Europe.

2.4. Allocation

2.4.1. Multi-output Allocation

Multi-output allocation generally follows the requirements of ISO 14044, section 4.3.4.2. When allocation becomes necessary during the data collection phase, the allocation rule most suitable for the respective process step is applied and documented along with the process in Chapter 3. No multi-output allocation has been applied for the foreground data used in this study. Allocation of background data (energy and materials) taken from the GaBi 2019 databases is documented online at <http://www.gabi-software.com/international/databases/gabi-databases/>

2.4.2. End-of-Life Allocation

End-of-Life allocation generally follows the requirements of ISO 14044, section 4.3.4.3. Such allocation approaches address the question of how to assign impacts from virgin production processes to material that is recycled and used in future product systems.

Two main approaches are commonly used in LCA studies to account for end of life recycling and recycled content.

- Substitution approach (also known as 0:100, closed-loop approximation, recyclability substitution or end of life approach) – this approach is based on the perspective that material that is recycled into secondary material at end of life will substitute for an equivalent amount of virgin material. Hence a credit is given to account for this material substitution. However, this also means that burdens equivalent to this credit should be assigned to scrap used as an input to the production process, with the overall result that the impact of recycled granulate is the same as the impact of virgin material. This approach rewards end of life recycling but does not reward the use of recycled content.
- Cut-off approach (also known as 100:0 or recycled content approach) – burdens or credits associated with material from previous or subsequent life cycles are not considered i. e., are “cut-off”. Therefore, scrap input to the production process is considered to be free of burdens but, equally, no credit is received for scrap available for recycling at end of life. This approach rewards the use of recycled content but does not reward end of life recycling.

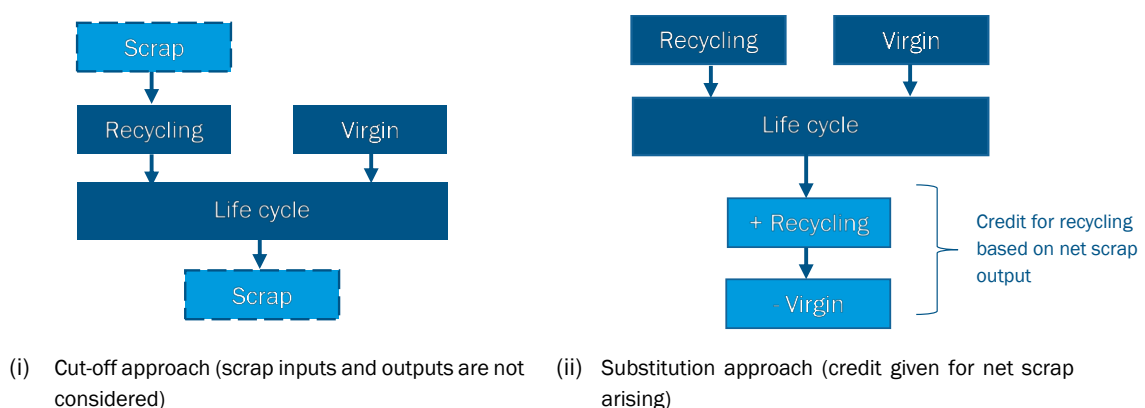


Figure 2-2: Schematic representations of the cut-off and substitution approaches

The substitution approach has been chosen as the allocation approach for the EoL due to the recovery of several materials. The paragraphs below describe in more detail what has been accounted in the EoL stage.

Material recycling (substitution approach): the lead used in the manufacturing of the batteries can come from two main routes, secondary and primary. The secondary lead dataset has opened EoL battery and secondary materials inputs. After collection of the current batteries at the EoL stage, a recycling process is applied. The original burden of the primary material input (lead in batteries and car cabling) is allocated between the current and subsequent life cycle using the mass of recovered secondary lead to scale the substituted primary material. The batteries EoL allocation approach applied is described in greater detail in the LCI section.

LFP batteries contain no economically valuable metals and thus have very low incentive for recycling. For other lithium ion battery chemistries, such as NMC, economic incentives for material recycling varies, but cobalt and nickel content are typically the primary driving factors.

When recycled today, to meet the 50% recycling efficiency targets of the Battery Directive 2006/66/EC, LFP cells are usually mixed with other battery chemistries with larger amounts of valuable materials to ensure that the total recycling efficiency of the recovery process meets requirements. In some cases, where including in a recycling process is not possible, LFP cells may be sent for incineration and burnt for energy recovery.

Typically, after collection, all lithium ion batteries are dismantled; the cells are removed from the rest of the pack, and the structural material and electronics in the packs are sent to separate recycling. In general, it is not economically viable to recover the materials lithium, iron and phosphate from the cathode of the LFP battery system and produce LiFePO_4 again. Therefore, for this study the recycling efficiency of the LiB LFP is estimated from maximum recycling possible from the other battery components, which represent approximately 30% of the battery. It is recognised that lithium ion battery recycling is in its infancy and in the future, it may be technically feasible to increase the recycling efficiency of processes for recovering materials from spent LFP batteries. Therefore, a scenario analysis has been completed (section 5.4) considering the technical potential for future recovery of materials in LFP cells. It must be stressed that although such processes could provide benefits through reducing the extraction and refining of virgin sources, it is unlikely that such processes will be economically driven and may not produce battery grade materials that can be reused in new battery manufacturing.

There is ongoing research and development to improve the recycling of lithium ion batteries. The cathode (active material) is treated in the hydrometallurgical process after all these separation processes⁷. They also state that the other materials after disassembly of the battery will have a higher recovery rate separately, e. g. stainless steel or copper.

Other lithium recovery from LFP cathodes are possible, but not common. One of these, is the acid leaching of the LFP with different precipitation stages where the output of the process is lithium carbonate and iron phosphate. This process brings the LFP into a solution with sulfuric acid (as it is done for lithium recover out of spodumene) where in the end, lithium carbonate is received through a precipitation process. In earlier stages FePO_4 would be precipitated.

The lithium carbonate could then be reused as an input material into new batteries if the required purity of the carbonate can be assured and the secondary residues can be dealt with.

⁷ <https://www.oeko.de/oekodoc/1500/2011-068-de.pdf>

At the University of Fuzhou in China, a research has been conducted where the final products are Li_3PO_4 and FePO_4 ⁸. As stated by the author in the conclusion of this report, this could be a process feasible for industrial applications, but there is doubt in terms of the volumes.

Ferro-Phosphorus could be produced in EAF / SAF and can then be used in the manufacture of high phosphorus steels, but more detailed research needs to be done about the FePO_4 produced from the recycling process.

Additionally, the following parameters are to be considered in the modelling of the batteries respectively:

- The recycled content of the active material in the batteries is 75% for Pb (25% primary and 75% secondary routes) and 0% for lithium (mainly primary materials are used).
- The collection rate for all battery types is assumed to be the same as reported for lead batteries (i.e. 97.3%),⁹
- Recycling efficiency based on battery weight is 82.7% (reference data)¹⁰ for PbB, and 30% for LiB (estimated from the BOM, and assuming that currently no recycling of the LFP cells occurs).

Energy recovery (substitution approach): In cases where materials are sent to waste incineration, they are linked to an inventory that accounts for waste composition and heating value as well as for regional efficiencies and heat-to-power output ratios. Credits are assigned to power and heat outputs substituting the regional grid mix and thermal energy from natural gas. The latter represents the cleanest fossil fuel and therefore results in a conservative estimate of the avoided burden.

Landfilling (substitution approach): In cases where materials are sent to landfills, they are linked to an inventory that accounts for waste composition, regional leakage rates, landfill gas capture, and utilisation rates (flaring vs. power production). A credit is assigned for power output substituting the regional grid mix.

2.5. Cut-off Criteria

No specific cut-off criteria are defined for the foreground of this study. As summarized in section 2.3, the system boundary was defined based on relevance to the goal of the study. For the processes within the system boundary, all available energy and material flow data have been included in the model. In cases where no matching life cycle inventories are available to represent a flow, proxy data have been applied based on conservative assumptions regarding environmental impacts.

The choice of proxy data is documented in the LCI chapter. The influence of these proxy data on the results of the assessment has been carefully analysed and is discussed in the LCI Chapter.

Cut-off-criteria applied to background data (energy and materials) taken from the GaBi 2020 databases is documented online (Sphera Solutions Inc., 2020).

2.6. Selection of LCIA Methodology and Impact Categories

The impact assessment categories and other metrics considered to be of high relevance to the goals of the project are shown in Table 2-5 and Table 2-6.

⁸ Huan Li et al.; Fuzhou University; <https://link.springer.com/article/10.1007/s11581-019-03070-w>

⁹ IHS recycling An Analysis of EU Collection and Recycling of Lead Based Automotive Batteries During the Period 2015-2017 2019

¹⁰ COMMISSION STAFF WORKING DOCUMENT on the evaluation of the Directive 2006/66/EC on batteries and accumulators and waste batteries and accumulators and repealing Directive 91/157/EEC

Various impact assessment categories are applicable for use in the European context including e. g. CML and selected impact categories recommended by the ILCD. This assessment is predominantly based on the CML impact categories (CML 2001 update April 2015). CML characterisation factors are applicable to the European context, are widely used and respected within the LCA community, and required for Environmental Product Declarations under EN 15804.

The Product Environmental Footprint (PEF) method (European Union, 2013), which is being developed by the European Commission and is currently in the transition phase, requires compliant assessments to take account of 15 LCIA methods. The use of a predefined list of impact categories is aimed at driving comparability between assessments of different products. Given the potential importance of PEF for European businesses in the future, these methods were considered for inclusion in this study. However, several the methods are currently not considered to be very mature (Lehmann, Bach, & Finkbeiner, 2016) and remain either in revision or awaiting update.

Given these issues, the CML impact categories are favoured in this study as these are well-established and remain the impact methodologies favoured by the metals industry for the European context (PE International, 2014). Global warming potential, renewable and non-renewable primary energy demand were chosen because of their relevance to climate change and energy efficiency, both of which are of high public and institutional interest. The global warming potential impact category is assessed based on the current IPCC characterisation factors taken from the 5th Assessment Report (IPCC, 2013) for a 100 year timeframe (GWP100) as this is currently the most commonly used metric¹¹.

Eutrophication, acidification, and photochemical ozone creation potentials were chosen because they are closely connected to air, soil, and water quality and capture the environmental burdens associated with commonly regulated emissions such as NO_x, SO₂, VOC, and others.

Human toxicity and ecotoxicity are not assessed in this study, while the state-of-the-art method is the USEtox™ characterization model. USEtox™ is currently the best-available approach to evaluate toxicity in LCA and is the consensus methodology of the UNEP-SETAC Life Cycle Initiative. The precision of the current USEtox™ characterization factors is within a factor of 100–1,000 for human health and 10–100 for freshwater ecotoxicity (Rosenbaum, et al., 2008). This is a substantial improvement over previously available toxicity characterization models, but still significantly higher than for the other impact categories noted above. Given the limitations of the characterization models for each of these factors, results are not to be used to make further comparative assertions.

The *Montreal Protocol on Substances that Deplete the Ozone Layer* was implemented in 1989 with the aim of phasing out emissions of ozone depleting gases. The protocol has been ratified by *all* members of the United Nations – an unprecedented level of international cooperation. With a few exceptions, use of CFCs, the most harmful chemicals have been eliminated, while complete phase out of less active HCFCs will be achieved by 2030. As a result, it is expected that the ozone layer will return to 1980 levels between 2050 and 2070. In addition, no ozone-depleting substances are emitted in the foreground system under study. For these reasons, ozone depletion potential is not considered in this study.

The present study excludes the assessment of resources. Resource shortages are driven by various factors that are not captured well by current metrics. Accordingly, resource criticality has emerged as a separate tool to assess resource consumption (Nassar, et al., 2012; Graedel & Reck, 2015). As a complete criticality assessment is out of scope for this work this impact category has been excluded from the assessment.

¹¹ The climate change methodology used in EF 3.0 is based on the latest IPCC reports but also includes the effects of “climate-carbon feedback” which results in higher global warming potentials but is also associated with greater uncertainty. In this study we have used the more commonly applied emission factors from the same report that exclude climate-carbon feedback effects.

In general, impacts related to resource depletion, toxicity to humans and ecosystems, land use change, and water scarcity are not recommended to be reported for metal LCAs. Among these, all are labelled as level II or III within the ILCD handbook (JRC, 2010), meaning that they are recommended by ILCD but in need of some improvements or to be applied with caution. Although these impacts are relevant environmental concerns, it is the position of the metal industry that the characterization of these impacts from the inventory data does not adequately support decision-making. As the supporting science improves and the LCI data becomes more robust (e. g., higher spatial resolution), inclusion of these impact categories should be periodically reconsidered. (Hendry, 2016).

Given the importance of mineral resources for society and the persistent debate about how mineral resource use should be addressed in life cycle assessment (LCA), a wide variety of impact assessment methods have been developed, each of which assesses different aspects of mineral resource use. Within the “global guidance for life cycle impact assessment (LCIA) indicators and methods” project of the Life Cycle Initiative hosted by UN Environment; a task force has been established to develop recommendations on the LCIA of mineral resource use. (Berger, 2020) and (Sonderegger, 2020)

Table 2-5: Impact category descriptions

Impact Category	Description	Unit	Reference
Global Warming Potential (GWP 100)	A measure of greenhouse gas emissions, such as CO ₂ and methane. These emissions are causing an increase in the absorption of radiation emitted by the earth, increasing the natural greenhouse effect. This may in turn have adverse impacts on ecosystem health, human health and material welfare.	kg CO ₂ equivalent	(IPCC, 2013)
Eutrophication Potential	Eutrophication covers all potential impacts of excessively high levels of macronutrients, the most important of which nitrogen (N) and phosphorus (P). Nutrient enrichment may cause an undesirable shift in species composition and elevated biomass production in both aquatic and terrestrial ecosystems. In aquatic ecosystems increased biomass production may lead to depressed oxygen levels, because of the additional consumption of oxygen in biomass decomposition.	kg PO ₄ ³⁻ equivalent	(Guinée, et al., 2002)
Acidification Potential	A measure of emissions that cause acidifying effects to the environment. The acidification potential is a measure of a molecule's capacity to increase the hydrogen ion (H ⁺) concentration in the presence of water, thus decreasing the pH value. Potential effects include fish mortality, forest decline and the deterioration of building materials.	kg SO ₂ equivalent	(Guinée, et al., 2002)
Photochemical Ozone Creation Potential (POCP)	A measure of emissions of precursors that contribute to ground level smog formation (mainly ozone O ₃), produced by the reaction of VOC and carbon monoxide in the presence of nitrogen oxides under the influence of UV light. Ground level ozone may be injurious to human	kg C ₂ H ₄ equivalent	(Guinée, et al., 2002)

Impact Category	Description	Unit	Reference
	health and ecosystems and may also damage crops.		

Table 2-6: Other environmental indicators

Indicator	Description	Unit	Reference
Primary Energy Demand (PED)	A measure of the total amount of primary energy extracted from the earth. PED is expressed in energy demand from non-renewable resources (e. g. petroleum, natural gas, etc.) and energy demand from renewable resources (e. g. hydropower, wind energy, solar, etc.). Efficiencies in energy conversion (e. g. power, heat, steam, etc.) are considered.	MJ (lower heating value)	(Guinée, et al., 2002)

It shall be noted that the above impact categories represent impact *potentials*, i.e., they are approximations of environmental impacts that could occur if the emissions would (a) actually follow the underlying impact pathway and (b) meet certain conditions in the receiving environment while doing so. In addition, the inventory only captures that fraction of the total environmental load that corresponds to the functional unit (relative approach). LCIA results are therefore relative expressions only and do not predict actual impacts, the exceeding of thresholds, safety margins, or risks.

In this study, no grouping or further quantitative cross-category weighting has been applied. Instead, each impact is discussed in isolation, without reference to other impact categories, before final conclusions and recommendations are made.

2.7. Interpretation to Be Used

The results of the LCI and LCIA were interpreted according to the goal and scope. The interpretation addresses the following topics:

- Identification of significant findings, such as the main process step(s), material(s), and/or emission(s) contributing to the overall results
- Evaluation of completeness, sensitivity, and consistency to justify the exclusion of data from the system boundaries as well as the use of proxy data
- Conclusions, limitations and recommendations

2.8. Sensitivity and Scenario Analysis

Sensitivity and scenario analyses compare results between discrete sets of parameter settings or model choices. During the data collection some parameters were identified as possible variations from the baseline considered according to the references consulted. The following sensitivity and scenario analysis have been done:

- LFP battery weight variation (from 12 kg to 10 kg) including electronics but excluding the crash protection
- LFP battery lifetime (baseline 8 years), however a scenario with 10 and 15 years has been tested

- It has been assumed that same energy/fuel savings for PbB and LiB in start-stop and micro-hybrid. Nevertheless, an assumption has been made and is tested via a scenario analysis where 1% benefit for LiB vs PbB.
- Vehicle lifetime base scenario considers 10 years. As an alternative scenario, 15 years is analysed
- An EoL scenario on recycling efficiency; where a variation of 50% for LFP batteries is tested by comparing the baseline with potential future recycling process (currently not applied commercially)
- A sensitivity analysis about the cut-off EoL approach have been done

Sensitivity and scenario analysis results are shown in section 5.3 and 5.4.

2.9. Data Quality Requirements

The data used to create the inventory model shall be as precise, complete, consistent, and representative as possible with regards to the goal and scope of the study under given time and budget constraints.

- Measured primary data are of the highest precision, followed by calculated data, literature data, and estimated data. The goal is to model all relevant foreground processes using measured or calculated primary data for PbB and secondary data for LiB based on the sector expertise and valuable publications.
- Completeness is judged based on the completeness of the inputs and outputs per unit process and the completeness of the unit processes themselves. The goal is to capture all relevant data in this regard.
- Consistency refers to modelling choices and data sources. The goal is to ensure that differences in results reflect actual differences between product systems and are not due to inconsistencies in modelling choices, data sources, emission factors, or other artefacts.
- Reproducibility expresses the degree to which third parties would be able to reproduce the results of the study based on the information contained in this report. The goal is to provide enough transparency with this report so that third parties can approximate the reported results. This ability may be limited by the exclusion of confidential primary data and access to the same background data sources.
- Representativeness expresses the degree to which the data matches the geographical, temporal, and technological requirements defined in the study's goal and scope. The goal is to use the most representative primary data for all foreground processes and the most representative industry-average data for all background processes. Whenever such data were not available (e.g., no industry-average data available for a certain country), best-available proxy data were employed.

An evaluation of the data quality with regards to these requirements is provided in the LCI Chapter.

2.10. Type and format of the report

In accordance with the ISO requirements (ISO, 2006), this document aims to report the results and conclusions of the LCA completely, accurately and without bias to the intended audience. The results, data, methods, assumptions and limitations are presented in a transparent manner and with sufficient detail to convey the complexities, limitations, and trade-offs inherent in the LCA to the reader. This allows the results to be interpreted and used in a manner consistent with the goals of the study.

It is intended that the results of the study will be made available to a wider audience through the EUROBAT and ILA websites and it is the intention that the life cycle inventories will be made available to users of the GaBi LCA software through the GaBi professional database.

2.11. Software and Database

The LCA model was created using the GaBi 9 Software system for life cycle engineering, developed by Sphera GmbH. The GaBi 2019 LCI database provides the life cycle inventory data for several of the raw and process materials obtained from the background system.

2.12. Critical Review

In accordance with ISO 14044 section 6.3 and ISO/TS 14071, a critical review of this study is undertaken in two parts, goal and scope and full report by Matthias Finkbeiner (panel chair) from Technical University Berlin, Germany to ensure conformity with ISO 14040/44, and Jeff Spangenberg and Qiang Dai from Argonne National Lab and Eberhard Meissner, battery specialist. The critical review of the external expert is performed after completion of the study. The analysis and the verification of software model and individual datasets are outside the scope of this review.¹²

The Critical Review Statement will be found in Annex A. The Critical Review Report containing the comments and recommendations by the independent experts as well as the practitioner's responses is available upon request from the study commissioner in accordance with ISO/TS 14071.

¹² Reviewers were not engaged or contracted as official representative of their organization but acted as independent expert reviewers.

3. Life Cycle Inventory Analysis

3.1. Data Collection Procedure

The following paragraphs describe the data collected and used for all life cycle stages modelling, and the most relevant references are listed.

3.1.1. Lead Battery

Average primary data was collected in the context of the ongoing European LCA Lead batteries study commissioned by ILA reviewed by Matthias Finkbeiner from Technical University Berlin, Germany to ensure conformity with ISO 14040/44, Jeff Spangenberg and Qiang Dai from Argonne National Lab (thinkstep, 2019b).

3.1.2. LFP Battery

The data collection for LFP battery was undertaken by initially reviewing available literature for appropriate data-specifically:

- Ricardo (2020) Lead Battery Automotive Trends Review-Final Report RD19-001611-11
- A123 UltraPhosphate lithium Ion 12 V starter battery specifications downloaded from <http://www.a123systems.com/automotive/products/systems/12v-starter-battery/> on 18/6/2020
- Previous ELV Annex II (2014) submissions on lithium ion starter batteries by Contribution of A123 Systems, Fraunhofer, LG Chem and Samsung SDI
- Input from lead battery expert Geoffrey May, Focus consulting
- Input from companies who produce lithium ion batteries within membership of EUROBAT and Consortium for Battery Innovation
- PEFCR - Product Environmental Footprint Category Rules for High Specific Energy Rechargeable Batteries for Mobile Applications (Recharge, 2018)

This information was then reviewed and approved by the members European Car Manufacturers Association (ACEA), the Japanese Car Manufacturers Association (JAMA) and The Korean Car Manufacturers Association (KAMA).

3.2. Production Stage

3.2.1. Lead Battery

Manufacturers' data were weighted based on production volumes to create average batteries, which were then scaled to the average battery weight defined in Table 3-1. It lists the inputs and outputs associated with the production of each battery, including all processes and on-site wastewater treatment. All lead and lead alloy compounds are derived from primary and secondary production of lead. Water sent through on-site wastewater treatment was subsequently sent to municipal wastewater treatment.

The following emissions to air, if not reported by a company, were approximated using the average of all other reporting companies: sulfuric acid vapor, lead, antimony, arsenic, dust, and VOCs. All other emissions were either reported by companies or, as in the case of combustion emissions, included by using the

relevant GaBi datasets. For emissions to water, arsenic, cadmium, copper, and lead were approximated using an average of other companies if not reported by a site.

Table 3-1: Average gate-to-gate data for one production volume average Lead batteries

Type	Flow	Standard	Improved	Advanced	Unit
Input	Lead (incl. alloys, red lead and oxide)	10.5	10.2	11.7	kg
	Glass fibres	6.30E-03	1.16E-03	0.03	kg
	Polyethylene part (PE)	0.38	0.19	0.25	kg
	Polypropylene part (PP)	0.76	0.59	0.77	kg
	Secondary Polypropylene	0.18	0.15	0.12	kg
	Sodium sulphate	2.42E-03	1.78E-04	3.56E-04	kg
	Sulfuric acid (100%)	4.35	3.23	3.70	kg
	Water (desalinated; deionised)	4.74	3.90	3.33	kg
	Water (ground water)	52.2	20.1	17.6	kg
	Water (tap water)	8.68	13.9	13.1	kg
	Electricity	38.3	35.9	35.9	MJ
	Thermal energy from natural gas	35.5	31.3	51.2	MJ
	Iron Chloride for WWT	2.42E-02	0	3.47E-03	kg
	Flocculants for WWT	8.89E-03	0.01	3.44E-04	kg
	Sodium hydroxide incl. for WWT	6.89E-03	0.03	0.84	kg
Output	Lead acid battery	18	19	20	kg
	Lead scrap	0.74	1.31	0.57	kg
	Hazardous waste for further processing	9.97E-03	2.73E-03	0.014	kg
	Waste for recovery	0.61	1.32	0.58	kg
	Wastewater to municipal treatment	13.06	9.46	12.5	kg
Emissions to air	Dust (>PM10)	4.59E-04	4.37E-04	2.27E-04	kg
	Lead	3.57E-05	3.55E-04	1.87E-06	kg
	Sulfuric acid	1.98E-04	1.98E-05	7.95E-05	kg
	Nitrogen dioxide	2.08E-04	1.07E-04	5.02E-06	kg
	Water vapour	9.59	7.73	9.20	kg
	Nickel	2.88E-08	6.46E-09	2.39E-08	kg

Emissions to water	Zinc	3.31E-07	1.9E-08	6.25E-08	kg
	Sulphate	9.29E-03	8.23E-03	1.12E-02	kg
	Lead	4.99E-06	2.65E-06	2.33E-06	kg
Other (application level)	Cabling car (Polypropylene / copper wire)	0.7	0.7	0.7	kg

3.2.2. LFP battery

It was not possible to obtain manufacturers' data for 12V automotive LFP batteries currently on the market.

Table 3-2 lists the bill of material and production data for one LFP battery that was constructed as described in section 3.1.2.

Table 3-2 lists the bill of material and production data for one LFP battery. The production data (electricity, emissions to air and auxiliary materials have been calculated considering the values reported in the PEFCR - Product Environmental Footprint Category Rules for High Specific Energy Rechargeable Batteries for Mobile Applications (Recharge, 2018). As referenced in the same PEFCR an increase of 5% of the cell mass components amounts and 3% increase for passive components have been considered to include direct manufacturing wastes. The respective manufacturing wastes have been treated as described in the End of Life Section 2.4.2.

Table 3-2: Bill of Material and production data for one LFP battery

Input parameter	Amount	Unit
ASSEMBLY DATA		
Energy		
Electricity CN ¹³ (cell electrodes production & forming)	492	MJ
Electricity EU ¹⁴ (battery assembly)	2.4	MJ
Emissions to air		
Dust to air	190	µg
SO ₂ to air	72	µg
NO _x to air	1.0	µg
Auxiliary materials		
Water deionized (anode + production)	4.4	kg
N-Methylprolidone (cathode)	1.7	kg
Waste treatment in manufacturing		
Total 5% of cell weight	0.42	kg
Plastic (battery case + other internal components)	0.045	kg

¹³ Electricity grid mix for China

¹⁴ Electricity grid mix for Europe

Internal clamps, Stainless steel	0.006	kg
Copper wire	0.012	kg
Electronics	0.045	kg
BATTERY COMPONENTS		
Total battery weight (w/o) crash protection and car cabling	12.0	kg
Anode		
Copper foil	1.09	kg
Graphite	1.01	kg
Cathode		
Al	0.67	kg
LFP	2.28	kg
Carbon black	0.12	kg
Binder (PVDF)	0.12	kg
Electrolyte		
EC/DMC	1.26	kg
LiPF ₆	0.25	kg
Separator		
PP	0.5	kg
Cell case, foil pouch		
Al	1.09	kg
Battery case		
Polypropylene	1	kg
Passive components		
Internal clamps, fastenings (stainless steel)	0.20	kg
Internal connectors and terminals (copper)	0.40	kg
Connectors & cables	0.40	kg
EMC Shielding	0.50	kg
Electronic circuit boards	0.40	kg
Power semiconductor	0.08	kg
Plastic part	0.12	kg
Other components (PP)	0.50	kg
External accessories for LFP (not included in battery weight, calculated in Manufacturing results)		
Crash protection (Steel sheet)	3	kg
Cabling car (Polypropylene / copper wire)	0.7	kg

3.3. Use stage

The use stage has been modelled considering the available information from the automotive sector, nevertheless, the authors acknowledge other factors that might contribute to these savings, such as other vehicle components' weight (apart from battery components) and the drivers' behaviour.

Table 2-1 and Table 2-2 define the characteristic lifetime and fuel consumptions for three battery-applications. This data was provided by the study participants based on prevalent standard averages in

the automotive industry. The data refers to a 'Small MPV', as it is referred to in Euro NCAP¹⁵ classification. These vehicles fall under category M1 vehicles as defined by the European Commission (passenger vehicles with no more than 8 seats, weighing less than 3.5 tonnes).¹⁶

Although the battery is an integral component of start-stop and micro-hybrid systems, it is not possible to isolate its specific contribution to these fuel reduction values. Other components are also installed in start-stop and micro-hybrid systems including starter and ring-gear reinforcement, the installation of a battery state sensor plus wires/connectors, additional sensors for gear shift neutral and pedal position, and restart voltage quality countermeasures (i.e. a dc/dc converter). Therefore, the given fuel reduction values refer to an overall system level. These total savings are attributed to the battery for the purposes of this study (best case assumption) as the key enabler for storing and releasing the vehicle's energy within the start-stop/micro-hybrid system.

This study attempts to isolate the contribution of the start-stop/micro-hybrid system (of which improved or advanced technology lead-based batteries are an integral part) from other technologies used to improve fuel efficiency within the vehicle i.e. base engine updates, engine downsizing, reduced roll resistance tires, vehicle weight reduction, and aerodynamic improvements. From current information, the specific contribution of the start-stop/micro-hybrid system to the vehicle's overall reduction in fuel consumption can range from 3-9.5%, dependent on the system type provided. Improved or advanced technology lead-based batteries are an essential part of these systems, with the required type and performance differing significantly in conventional vehicles. Stop-Start and Micro-hybrid vehicles and their deep-cycle resistance and charge recoverability are progressively increasing.

To avoid overestimation or bias, this study assumes a conservative 4% reduction in fuel consumption from the installation of start-stop systems using improved technology batteries, and an 8% reduction in fuel consumption from installation of Micro-hybrid systems (start-stop, regenerative braking, passive boosting) using advanced technology batteries¹⁷. (EPA, 2016)

These assumptions are applied to the reference case, a representative compact MPV using a standard technology battery, with fuel efficiency of 5.1 litre/km¹⁸. A representative lifetime of 10 years and/or 150,000 km has also been assumed and is in line with the parameters selected as standard by the car industry for several vehicle LCAs¹⁹.

In the use stage, the weight difference between the PbB and LiB LFP has been accounted for in the calculation of results. Table 3-3 shows the additional gasoline amounts considered; these were calculated based on fuel reduction formula published by Volkswagen. (Christoph Koffler, 2009)

'It has been shown that the fuel consumption required to move a mass of 100 kg over 100 km, can be obtained based on the NEDC driving cycle and the differential efficiency of gasoline and diesel engines'. . . It has also been shown that it is advisable to utilize mass differences rather than mass ratios when calculating the lightweight effect on fuel consumption during the use stage'. (Rohde-Brandenburger, On the calculation of fuel savings through lightweight, 2009)

*Gasoline consumption per kg weight: $0.35 \text{ l}/(100 \text{ km} \cdot 100 \text{ kg}) \rightarrow 3,885 \text{ kg}/150,000 \text{ km}$
Gasoline specific density (used for conversion from Litre to kg): 0.74 kg/l*

¹⁵ 'Small MPV' is a Euro NCAP structural-class classification (http://www.euroncap.com/small_mpv.aspx)

¹⁶ The ELV directive (2000/53/EC) of the European Commission is applicable to category M1 vehicles. "vehicle' means any vehicle designated as category M1 or N1 defined in Annex IIA to Directive 70/156/EEC, and three-wheel motor vehicles as defined in Directive 92/61/EEC, but excluding motor tricycles" -

¹⁷ The Driving Force Behind Start-Stop, Innovative Start-Stop Batteries from VARTA, Johnson Controls. UK

¹⁸ Derived from average fuel consumption values for MPV from www.fuelmileage.co.uk

¹⁹ Automotive LCA Guidelines – Phase 2, EUCAR

Table 3-4 lists the emissions to air considered in the calculation of the use stage; these emissions correspond to a passenger car with a gasoline engine technology and with typical driving behaviour of MPV mainly in urban areas.

In the comparison of the use phase considering the weight difference between the LFP and PbB only fuel depending emissions like CO₂ and SO₂ have been considered. For limited emissions like CO, NO_x and NMVOC's there is no difference in emissions amount if more gasoline is used per km since the limitation of the emissions are related to the km. Therefore, only comparison between CO₂ and SO₂ during use phase is possible. Of course, for the fuel production (exploration until the point of use) itself CO, NO_x, NMVOC are depending on the volume of gasoline produced.

Table 3-3: Additional fuel consumption due to battery weight difference

Application	PbB weight (kg)	LiB LFP with crash protection weight (kg)	Weight difference (kg)	Add. fuel consumption for PbB per FU (kg)
Conventional ICE	18	15	3	11.66
Start-stop	19	15	4	15.54
Micro-hybrid	20	15	5	19.43

Table 3-4: Combustion emission factors 1 kg gasoline consumed (passenger car)

Emission to air	Amount	Unit
Carbon dioxide	3.01	kg
Carbon dioxide (biotic) ²⁰	0.1 6	kg
Sulphur dioxide	2.0E-05	kg

3.4. End of Life Stage

3.4.1. LFP batteries EoL

In this study, the baseline was set with assuming pyrolysis for the LFP battery cells to recover energy from the incineration process. Material recovery was assumed for the BMS and battery housings and other components.

Today there are no commercial processes specifically designed for LFP cell recovery but rather LFP cells are mixed into the metallurgical processes where NMC batteries are recovered. And in this context an overall recovery of 50% as required by the EU Battery Directive can be achieved for LiB in general. This includes the BMS, housing, etc.

As described in section 2.4.2, the LFP battery cell is incinerated (with material and energy recovery as described in Table 3-5) and only the passive components, electronics, battery case are recycled. By doing so a recycling efficiency of 30% is achieved. The car cabling and crash protection is also recycled, but not included in the calculation of the recycling efficiency since these are considered as additional accessories

²⁰ EU-28 Gasoline dataset includes ~5% share of bio-components (bio-ethanol and bio-diesel).

for the correct function of the battery. (In the case of the PbB only car cabling is considered, since no crash protection is required).

A scenario was carried out by modelling a future metallurgical process that can recover the lithium and other components from LFP cells whilst neglecting the iron phosphate. Recovering the lithium and the aluminium foils and copper in the cells increases the recovery rate to approximately 40%.

Table 3-5: End of Life Cycle – LFP battery

Cell / battery component	Amount	Unit	EoL Treatment	Credits
Battery LFP Cell				
ANODE			Hazardous waste incineration with energy recovery The dataset covers all relevant process steps for the thermal treatment and corresponding processes, such as disposal of air pollution control residues or metal recycling. The system is partly terminated in order to consider credits (open outputs electricity and steam). Credits for recovered metals are already included.	Electricity / Thermal energy
Copper foil	1.09	kg		
Graphite	1.01	kg		
CATHODE				
Al	0.67	kg		
LFP	2.28	kg		
Carbon black	0.1 2	kg		
Binder (PVDF)	0.1 2	kg		
ELECTROLYTE				
EC/DMC	1.26	kg		
LiPF ₆	0.25	kg		
SEPARATOR				
PP	0.5	kg		
Cell case, foil pouch				
Al	1.09	kg		
Battery case				
PP	1	kg	recycling plastic granulate	Polypropylene granulate
Passive components (electronics)				
Internal clamps, fastenings (stainless steel)	0.20	kg	recycling	Stainless steel
Internal connectors and terminals (copper wire)	0.40	kg	recycling	Copper
Internal circuitry, PCB + components +internal wiring, some in metal cases	1.50	kg	shredding & recovery (>50% landfill / incineration & recycling)	Electricity & thermal energy / Copper / Palladium / Silver / Gold
Other internal components (PP)	0.50	kg	recycling plastic granulate	Polypropylene granulate
External accessories for LFP (not included in battery weight, calculated in EoL results)				
Cabling car	0.7	kg	metal recycling, plastic incineration	Copper / Electricity / Thermal energy
Crash protection	3	kg	metal recycling	Steel billet

3.4.2. Lead-based batteries EoL

The substitution approach (close loop recycling approach) was used to assess the impacts associated with the use of recycled lead from lead scrap in the batteries.

This approach connects the amount of scrap generated by the process to the amount of scrap demanded and compensates for any difference with additional lead production. Only the difference in lead leads to an impact or credit from secondary lead in the production stage. The burden of processing the secondary lead falls in the recycling stage.

On average, the lead used in the manufacturing of the batteries comes from two main routes: secondary 75% and 25% primary. The secondary lead dataset has opened EoL battery and secondary materials inputs. After collection of the current batteries, these are looped back to the production stage replacing the net amount of EoL batteries as input to the secondary lead dataset (recycling). The differences between supplied and resulting EoL battery mass values are compensated by sending the remaining amount to recycling in the EoL stage and a credit is applied. The car cabling recycling and recovery of copper and energy (plastic incineration) has also been considered. Figure 3-1 depicts the approach applied.

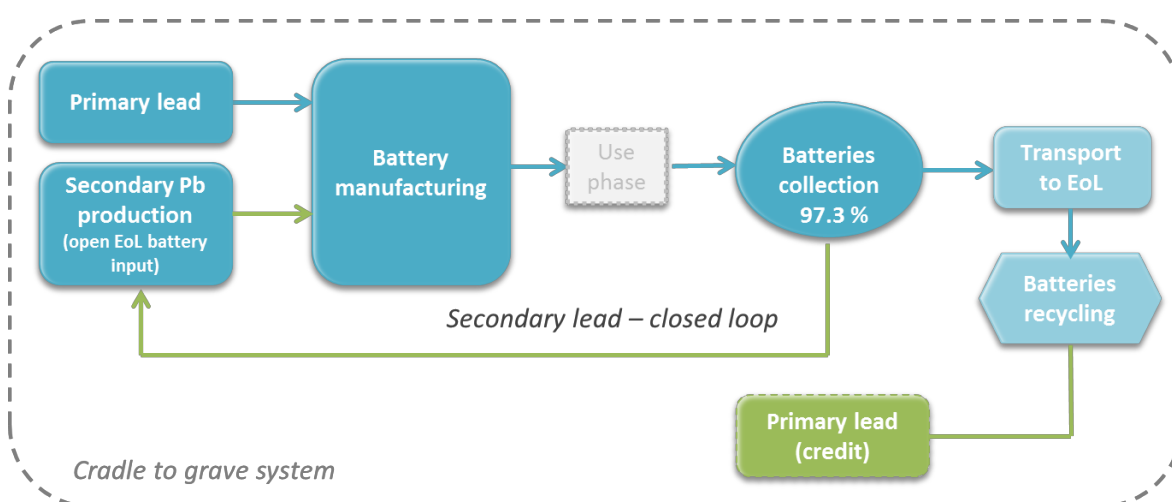


Figure 3-1: Lead batteries EoL – Material recycling (substitution approach)

3.5. Background Data

Documentation for all GaBi datasets can be found online (thinkstep, 2019a)

3.5.1. Fuels and Energy

National or regional averages for fuel inputs and electricity grid mixes were obtained from the GaBi 2019 databases. Table 3-6 shows the most relevant LCI datasets used in modelling the product systems. Electricity consumption for LiB batteries was modelled using China country grid mix for the battery cell production and EU-28 for the assembly of the battery components.

Table 3-6: Key energy datasets used in inventory analysis

Energy	Location	Dataset	Data Provider	Reference Year	Proxy?
Electricity	EU-28	Electricity grid mix	Sphera	2016	-

	CN	Electricity grid mix	Sphera	2016	-
Thermal energy	EU-28	Thermal energy from natural gas	Sphera	2016	-

3.5.2. Raw Materials and Processes

Data for upstream and downstream raw materials and unit processes were obtained from the GaBi 2019 database. Table 3-7 shows the most relevant LCI datasets used in modelling the product systems.

Table 3-7: Key material and process datasets used in inventory analysis for Lead Battery

Material / Process	Geo.	Dataset	Data Provider	Reference Year	Proxy?
Expander	DE	Barium sulphate (BaSO ₄)	Sphera	2018	-
Expander	DE	Carbon black (furnace black; general purpose)	Sphera	2018	-
Glass mat	DE	Glass fibres	Sphera	2018	-
LDPE	EU-28	Polyethylene Low Density Granulate (LDPE/PE-LD)	Sphera	2018	-
PP	EU-28	Polypropylene granulate (PP)	Sphera	2018	-
Lead, primary	EU/NAM	Primary lead average production mix	ILA	2015	-
Lead, secondary	EU	Secondary lead average production mix	ILA	2015	-
Sand	DE	Limestone flour	Sphera	2018	-
Sodium sulphate	GLO	Sodium sulphate	Sphera	2018	-
Sulfuric acid	DE	Sulphuric acid (high purity)	Sphera	2018	-
Deionized water	EU-28	Water deionized	Sphera	2018	-
Tap water	EU-28	Tap water from ground water	Sphera	2018	-
Car cabling	EU-28	Copper wire (0.06 mm)	Sphera	2018	-
Process related					
Hydrochloric acid (WWT)	DE	Hydrochloric acid 32%	Sphera	2018	-
Hazardous waste treatment	DE	Hazardous waste (statistic average) (no C, worst case scenario incl. landfill)	Sphera	2018	-
Ferric chloride (WWT)	DE	Ferric chloride 37%	Sphera	2018	-
Limestone (WWT)	DE	Limestone flour	Sphera	2018	-
Wastewater treatment	DE	Municipal wastewater treatment (mix)	Sphera	2018	-

Injection moulding	GLO	Plastic injection moulding (parameterized)	Sphera	2018	-
Soda (WWT)	DE	Sodium hydroxide (caustic soda) mix (100%)	Sphera	2018	-
Water	EU-28	Tap water from groundwater	Sphera	2018	-

Table 3-8: Key material and process datasets used in inventory analysis for LFP Battery

Material / Process	Geo.	Dataset	Data Provider	Reference Year	Proxy?
Cell material	CN	Lithium hydroxide	Sphera	2018	-
	US	Phosphoric acid (75%)	Sphera	2018	yes
	EU-28	Iron (II) sulphate	Sphera	2018	yes
	CN	Polyvinylidene fluoride (emulsion polymerization) (PVDF) - open inputs energy	Sphera	2018	-
	CN	Carbon Black	Sphera	2018	-
	GLO	Aluminium part	Sphera	2018	-
	GLO	Steel sheet part	Sphera	2018	-
	CN	Synthetic graphite via calcined petroleum coke	Sphera	2018	-
	GLO	Copper sheet part	Sphera	2018	-
	GLO	Dimethyl carbonate	Sphera	2018	-
	GLO	Aluminium part	Sphera	2018	-
	GLO	Water (desalinated; deionised)	Sphera	2018	-
	JP	Lithium Hexafluorophosphate (LiPF ₆)	Sphera	2018	-
	GLO	Cable 1-core signal 24AWG PE (4.5 g/m) D1.4	Sphera	2018	-
Electronics	GLO	Cable 3-core mains power 10A/13A 16AWG PVC (100 g/m) D8	Sphera	2018	-
	DE	Connector T-block (5-way, without Au, PA6.6 basis)	Sphera	2018	-
	GLO	Connector PATA	Sphera	2018	-
	GLO	Average Printed Wiring Board with Power Electronics (DfX-compatible)	Sphera	2018	-
	GLO	Average Printed Wiring Board with Signal-Power Electronics (DfX-Compatible)	Sphera	2018	-
	EU-28	Tap water from groundwater	Sphera	2018	yes

EoL	GLO	Transistor power THT/SMD SOT93/TO218 7 leads (4.80g) 15.5x12.9x4.7	Sphera	2018	-
	GLO	EMS Shielding	Sphera	2018	-
	EU-28	Gasoline mix (regular) at refinery	Sphera	2018	-
	EU-28	Copper scrap values (average scrap) - EoL recycling potential	Sphera	2018	-
	GLO	Recycling of stainless-steel scrap	Sphera	2018	-
	EU-28	Recycling of polypropylene (PP) plastic	Sphera	2018	-
	EU-28	Hazardous waste in waste incineration plant	Sphera	2018	-
	EU-28	Polypropylene granulate (PP) mix	Sphera	2018	-
	DE	Incineration of electronics scrap (Printed Wiring Boards, PWB)	Sphera	2018	-

3.5.3. Transportation

Average transportation distances and modes of transport are included for the transport of the raw materials, operating materials, and auxiliary materials to production facilities. Relevant datasets are shown in Table 3-9 and

Table 3-10.

Table 3-9: Transportation and road fuel datasets

Mode / fuels	Geographic Reference	Dataset	Data Provider	Reference Year	Proxy?
Class EU 4 truck	GLO	Truck-trailer, Euro 4, 28 - 34t gross weight / 22t payload capacity	Sphera	2018	-
Container ship	GLO	Container ship, 5,000 to 200,000 dwt payload capacity, ocean going	Sphera	2018	-
Diesel	EU-28	Diesel mix at refinery	Sphera	2016	-
Fuel oil	EU-28	Heavy fuel oil at refinery (1.0wt. % S)	Sphera	2016	-

Table 3-10: Use stage vehicle datasets

Mode / fuels	Geographic Reference	Dataset	Data Provider	Reference Year	Proxy?
--------------	----------------------	---------	---------------	----------------	--------

Passenger car (gasoline combustion)	GLO	Car petrol, Euro 4, engine size up to 1.4l ts (10 ppm sulphur, 5.60 wt.% bio components)	Sphera	2018	-
Gasoline (production)	EU-28	Gasoline mix (regular) at refinery	Sphera	2016	-

3.6. Life Cycle Inventory Analysis Results

ISO 14044 defines the Life Cycle Inventory (LCI) analysis result as the “outcome of a life cycle inventory analysis that catalogues the flows crossing the system boundary and provides the starting point for life cycle impact assessment”. As the complete inventory comprises hundreds of flows, the below table only displays a selection of flows based on their relevance to the subsequent impact assessment in order to provide a transparent link between the inventory and impact assessment results.

Table 3-11: LCI results of total battery life cycle per battery type and FU – Conventional ICE application (units in kg unless otherwise noted)

Type	Flow	Conventional ICE application	
		PbB Standard	LiB - LFP
Resources	Crude oil (resource) [MJ]	692	573
	Hard coal (resource) [MJ]	121	1405
	Lignite (resource) [MJ]	14.03	55.54
	Natural gas (resource) [MJ]	273	844
	Uranium (resource) [MJ]	95.58	164
	Renewable energy resources [MJ]	145	487
	Non-renewable elements	0.78	3.58
	Non-renewable resources	128	778
	Renewable resources	40989	479293
	Fresh water	0.005	0.15
	Ground water	198	280
	Lake water	-0.11	6.77
	Lake water to turbine	7.83	240
	Rainwater	617	879
	River water	189	586
	River water to turbine	410	16862
	Sea water	308	632
Emissions to air	Ammonia	3.05E-03	5.76E-03
	Carbon dioxide	78	217
	Carbon monoxide	0.07	0.41
	Nitrogen dioxide	2.22E-03	9.90E-04
	Nitrogen monoxide	6.09E-03	2.61E-03
	Nitrogen oxides	0.07	0.49

	Nitrous oxide (laughing gas)	1.49E-03	5.88E-03
	Sulphur dioxide	0.19	0.69
	Sulphur hexafluoride	1.57E-11	1.65E-11
	Sulphur oxides	7.20E-28	2.38E-16
	Lead	1.78E-04	6.72E-04
	Methane	0.14	0.56
	Methane (biotic)	1.72E-03	5.24E-03
	Dust (> PM10)	4.64E-03	1.57E-01
	Dust (PM10)	5.10E-05	-3.22E-05
	Dust (PM2.5 - PM10)	3.13E-03	1.13E-01
	Dust (PM2.5)	2.87E-02	9.10E-02
Emissions to water	Biological oxygen demand (BOD)	1.04E-03	2.98E-03
	Chemical oxygen demand (COD)	2.48E-02	1.55E-01
	Total dissolved organic bound carbon (TOC)	3.52E-05	1.41E-05
	Total organic bound carbon (TOC)	6.57E-04	7.04E-04
	Nitrate	4.94E-08	1.61E-07
	Nitrogen organic bound	2.37E-03	1.93E-03
	Phosphate	5.39E-04	3.54E-04
	Phosphorus	2.94E-05	2.28E-04
	Sulphate	2.57E-01	4.33E-01
	Sulphuric acid	7.06E-08	2.65E-07
	Collected rainwater to river	5.86E+00	2.51E+01
	Cooling water to river	8.33E+01	2.52E+02
	Processed water to groundwater	1.30E-01	9.67E+00
	Processed water to lake	7.52E-23	2.38E-11
	Processed water to river	1.50E+02	3.29E+02
	Turbined water to river	4.53E+02	1.72E+04

Table 3-12: LCI results of total battery life cycle per battery type and FU – Start-Stop application (units in kg unless otherwise noted)

Type	Flow	Start-Stop application	
		PbB Improved	LiB - LFP
Resources	Crude oil (resource) [MJ]	-11277	-11517
	Hard coal (resource) [MJ]	53.50	1361
	Lignite (resource) [MJ]	7.00	29.48
	Natural gas (resource) [MJ]	-1199	-576
	Uranium (resource) [MJ]	2.90	99.30
	Renewable energy resources [MJ]	-540	-173

	Non-renewable elements	0.28	3.14
	Non-renewable resources	40.23	674.10
	Renewable resources	-26144	415122
	Fresh water	0.006	0.15
	Ground water	119	241
	Lake water	-1.89	-0.60
	Lake water to turbine	0.02	234.03
	Rainwater	-9937	-9870
	River water	-1109	-816
	River water to turbine	-1275	15312
	Sea water	-123	337
Emissions to air	Ammonia	-1.97E-02	-1.69E-02
	Carbon dioxide	-888	-756
	Carbon monoxide	-0.19	0.16
	Nitrogen dioxide	1.70E-03	5.92E-04
	Nitrogen monoxide	1.01E-03	-2.56E-03
	Nitrogen oxides	-0.27	0.15
	Nitrous oxide (laughing gas)	-1.53E-02	-1.12E-02
	Sulphur dioxide	-0.28	0.25
	Sulphur hexafluoride	-5.64E-12	6.10E-12
	Sulphur oxides	9.20E-28	2.38E-16
	Lead	7.06E-04	6.27E-04
	Methane	-1.26	-0.83
	Methane (biotic)	-7.12E-03	-4.28E-03
	Dust (> PM10)	1.67E-03	1.55E-01
	Dust (PM10)	-2.65E-05	-8.73E-05
	Dust (PM2.5 - PM10)	-1.91E-02	9.10E-02
	Dust (PM2.5)	8.19E-03	7.78E-02
Emissions to water	Biological oxygen demand (BOD)	-1.49E-03	7.72E-04
	Chemical oxygen demand (COD)	-7.03E-02	6.17E-02
	Total dissolved organic bound carbon (TOC)	2.54E-05	1.41E-05
	Total organic bound carbon (TOC)	-9.01E-03	-9.03E-03
	Nitrate	-3.72E-08	8.14E-08
	Nitrogen organic bound	-4.36E-02	-4.48E-02
	Phosphate	-9.97E-03	-1.03E-02
	Phosphorus	-2.11E-04	-1.51E-05
	Sulfate	-5.93E-02	1.67E-01

	Sulphuric acid	-9.33E-08	1.02E-07
	Collected rainwater to river	4.02E+00	2.40E+01
	Cooling water to river	1.02E+01	9.51E+01
	Processed water to groundwater	9.23E-01	9.56E+00
	Processed water to lake	9.49E-23	2.38E-11
	Processed water to river	-1.02E+03	-8.48E+02
	Turbined water to river	-1.34E+03	1.55E+04

Table 3-13: LCI results of total battery life cycle per battery type and FU – Micro-hybrid application (units in kg unless otherwise noted)

Type	Flow	Micro-hybrid application	
		PbB Advanced	LiB - LFP
Resources	Crude oil (resource) [MJ]	-23147	-23607
	Hard coal (resource) [MJ]	54.30	1317
	Lignite (resource) [MJ]	6.00	3.41
	Natural gas (resource) [MJ]	-2542	-1997
	Uranium (resource) [MJ]	-9.71	34.96
	Renewable energy resources [MJ]	-1159	-832
	Non-renewable elements	0.45	2.69
	Non-renewable resources	33.38	569.73
	Renewable resources	-59608	350951
	Fresh water	0.007	0.15
	Ground water	169	202
	Lake water	5.15	-7.97
	Lake water to turbine	-4.31	228.25
	Rainwater	-20391	-20620
	River water	-2167	-2218
	River water to turbine	-2719	13763
	Sea water	-309	42
Emissions to air	Ammonia	-4.15E-02	-3.96E-02
	Carbon dioxide	-1834	-1729
	Carbon monoxide	-0.42	-0.10
	Nitrogen dioxide	1.41E-03	1.93E-04
	Nitrogen monoxide	-3.70E-03	-7.72E-03
	Nitrogen oxides	-0.58	-0.19
	Nitrous oxide (laughing gas)	-3.17E-02	-2.83E-02
	Sulphur dioxide	-0.65	-0.19
	Sulphur hexafluoride	-1.35E-11	-4.35E-12

	Sulphur oxides	1.25E-27	2.38E-16
	Lead	5.72E-05	5.83E-04
	Methane	-2.61	-2.22
	Methane (biotic)	-1.51E-02	-1.38E-02
	Dust (> PM10)	7.38E-04	1.53E-01
	Dust (PM10)	-5.14E-05	-1.42E-04
	Dust (PM2.5 - PM10)	-4.00E-02	6.90E-02
	Dust (PM2.5)	-5.23E-04	6.46E-02
Emissions to water	Biological oxygen demand (BOD)	-3.35E-03	-1.43E-03
	Chemical oxygen demand (COD)	-1.56E-01	-3.15E-02
	Total dissolved organic bound carbon (TOC)	2.93E-05	1.41E-05
	Total organic bound carbon (TOC)	-1.86E-02	-1.88E-02
	Nitrate	-9.04E-08	2.13E-09
	Nitrogen organic bound	-8.93E-02	-9.15E-02
	Phosphate	-2.04E-02	-2.10E-02
	Phosphorus	-4.41E-04	-2.59E-04
	Sulphate	-2.69E-01	-9.86E-02
	Sulphuric acid	-2.19E-07	-6.11E-08
	Collected rainwater to river	4.78E+00	2.28E+01
	Cooling water to river	1.28E+02	-6.23E+01
	Processed water to groundwater	2.79E+00	9.46E+00
	Processed water to lake	1.27E-22	2.38E-11
	Processed water to river	-2.12E+03	-2.03E+03
	Turbined water to river	-2.87E+03	1.39E+04

4. Life Cycle Impact Assessment

This chapter contains the results for primary energy demand, global warming potential, acidification potential, eutrophication potential, and photochemical ozone creation potential, as well as additional metrics defined in section 2.6. It shall be reiterated at this point that the reported impact categories represent impact potentials, i.e., they are approximations of environmental impacts that could occur if the emissions would (a) follow the underlying impact pathway and (b) meet certain conditions in the receiving environment while doing so.

LCIA results are therefore relative expressions only and do not predict actual impacts, the exceeding of thresholds, safety margins, or risks.

4.1. Overall Results Summary

Total results for the total life cycle of lead and LFP batteries are displayed in Table 4-1. Negative values in LCIA results are derived from the application of system expansion (environmental credits) in the model. This is a commonly applied methodological choice to address the recovery of secondary materials or energy avoiding its production through primary routes. System expansion is sometimes referred as an “avoided impact approach”. In this study, the negative results stem from the reduced fuel consumption due to some battery types and credits to the recovered materials after recycling in the EoL stage. The avoided fuel consumption and recycling credits lead in some cases to a higher credit than the environmental burdens associated with producing the batteries.

Table 4-1: Total Life Cycle LCIA for Lead and LFP batteries per vehicle application and FU

Impact / Indicator	Conventional ICE		Start-stop		Micro-hybrid	
	PbB	LiB - LFP	PbB	LiB - LFP	PbB	LiB - LFP
AP [kg SO ₂ eq.]	0.27	1.15	-0.51	0.4	-1.16	-0.34
EP [kg Phosphate eq.]	0.02	0.08	-0.104	-0.04	-0.22	-0.16
GWP [kg CO ₂ eq.]	83	243	-938	-788	-1944	-1818
POCP [kg Ethene eq.]	0.018	0.09	-0.098	-0.02	-0.206	-0.14
PED [MJ]	1341	3524	-12970	-10776	-26817	-25076
PED, non-renewable [MJ]	1196	3037	-12430	-10603	-25657	-24244
PED, renewable [MJ]	145	487	-540	-173	-1187	-832

4.2. Primary Energy Demand

Primary energy demand is the quantity of energy directly taken from the environment prior to undergoing any anthropogenic changes and can be renewable (e. g. solar, hydropower) or non-renewable (e. g. coal, natural gas).

How primary energy demand is calculated varies according to the type of energy source. For fossil and nuclear fuels, primary energy demand is calculated as the energy content of the raw material. Similarly, the primary energy demand of renewable fuels is based on the energy content of the biomass used. For renewable energy technologies that directly generate electricity such as wind power, hydropower, solar power and geothermal power, the primary energy calculation is based on the efficiency of the conversion

of the specific energy source (e. g. a wind turbine converts about 40% of the kinetic energy of the wind into electricity, so 1 MJ electricity requires around 2.5 MJ primary energy from wind).

In Table 4-2 the PED for the lead and LFP batteries according to the different, vehicle application and FU for each life cycle stage is displayed.

Table 4-2: Primary energy demand from ren. and non ren. Resources (PED) [MJ]

Life Cycle Stage	Conventional ICE		Start-stop		Micro-hybrid	
	PbB	LiB - LFP	PbB	LiB - LFP	PbB	LiB - LFP
Manufacturing stage	828	3890	589	3890	819	3890
Use stage	617	0	-13500	-14300	-27600	-28600
EoL	-104	-366	-59	-366	-36	-366
Total Life Cycle	1341	3524	-12970	-10776	-26817	-25076

As in the rest of analysed impact categories and indicators, the use stage dominates the overall results for the start-stop and micro-hybrid application. For the conventional ICE, the manufacturing stage is dominant for LFP and PbB. As described in section 3.3, the use stage refers to the fuel saving due to the battery technology on car level, independent of the battery chemistry. In the case of PbB the weight difference compared to LFP batteries has also been considered.

In Figure 4-1 the overall results per battery technology and vehicle application according to the functional unit is displayed.

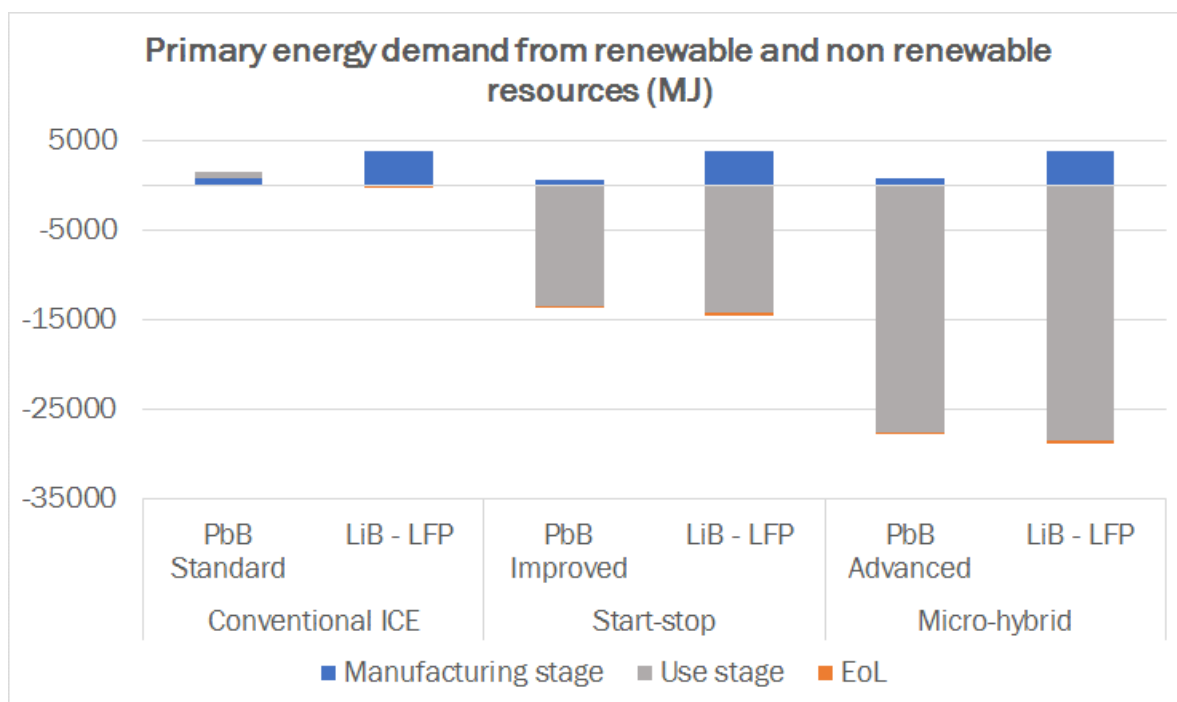


Figure 4-1: Overall Life Cycle PED per battery technology, vehicle application and FU

In Figure 4-2 the main contributors to the manufacturing stage are displayed.

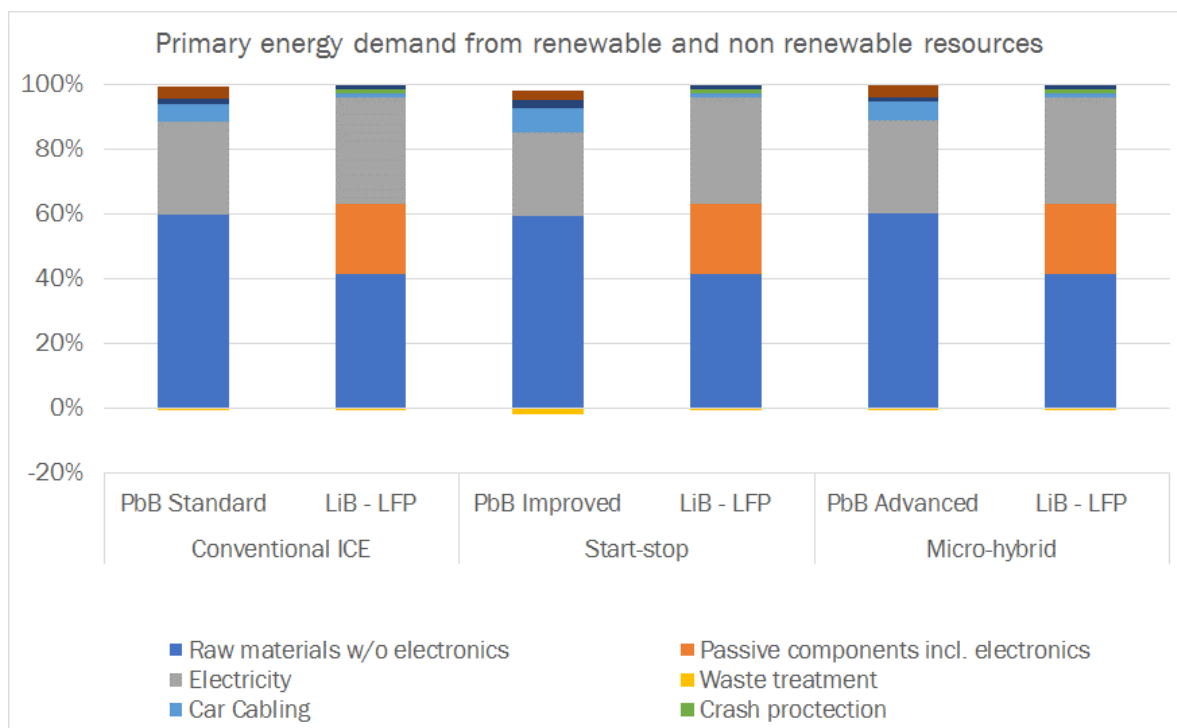


Figure 4-2: Main contributors to the PED (manufacturing stage) per battery technology, vehicle application and FU

For all battery types the manufacturing stage is dominated by the raw materials (approx. 60% for PbB and 40% for LiB - LFP) followed by electricity (approx. 25% for PbB and 35% for LiB - LFP). In the case of LiB - LFP the electricity is followed by the passive components including electronics (approx. 20%). Other components such as car cabling (approx. .5% for PbB and 1% for LiB - LFP) and crash protection (2%) have a lower contribution to the manufacturing stage results.

4.3. Global Warming Potential

As the name suggests, the mechanism of the greenhouse effect can be observed on a small scale in a greenhouse; incoming solar energy is trapped, causing the internal temperature to rise. This effect also occurs on a global scale. When short-wave ultraviolet radiation from the sun meets the Earth's surface some energy is re-emitted as longer wave infrared radiation. Instead of directly heading back out to space, some of this infrared radiation is absorbed by greenhouse gases in the troposphere and re-radiated in all directions, including back to earth. This results in a warming effect at the earth's surface. In addition to the natural mechanism, the greenhouse effect is enhanced by human activities. Greenhouse gases that are caused or increased, anthropogenically include, carbon dioxide, methane and CFCs. Since the residence time of the gases in the atmosphere is incorporated into the calculation, a time range for the assessment must also be specified; a period of 100 years is customary.

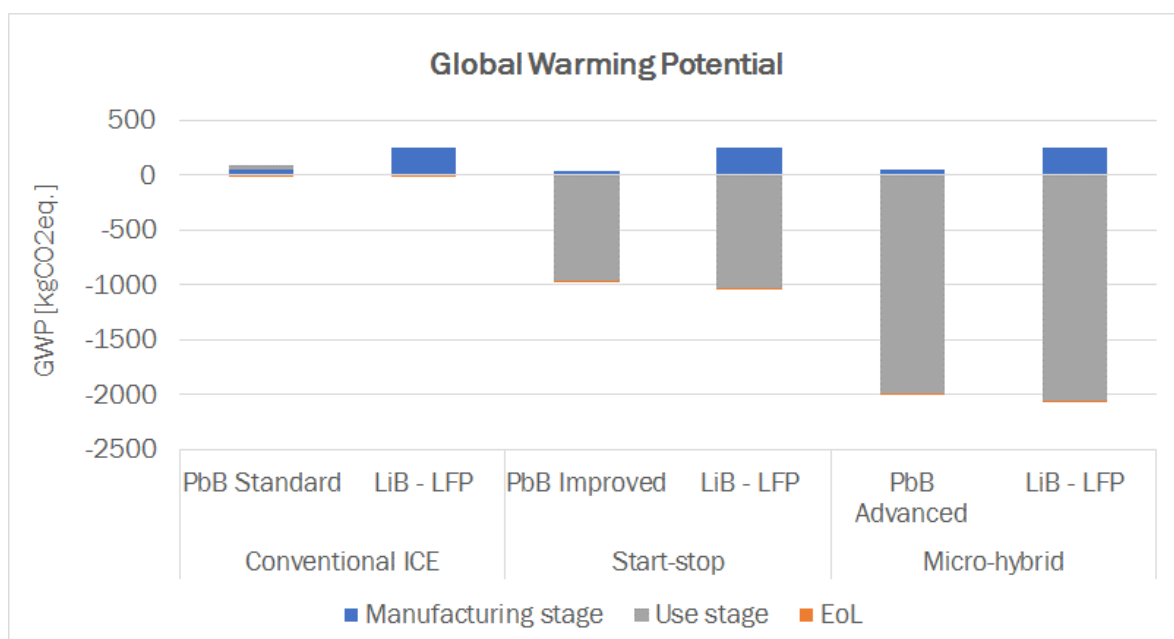
In Table 4-3 the GWP for the lead and LFP batteries according to the different technologies and vehicle application per FU for each life cycle stage is displayed.

Table 4-3: Global Warming Potential [kg CO₂ eq.]

Life Cycle Stage	Conventional ICE		Start-stop		Micro-hybrid	
	PbB	LiB - LFP	PbB	LiB - LFP	PbB	LiB - LFP
Manufacturing stage	45	254	35	254	47,8	254
Use stage	44	0	-970	-1030	-1990	-2060
EoL	-6	-12	-4	-12	-2	-12
Total Life Cycle	83	243	-938	-788	-1944	-1818

As in the rest of analysed impact categories and indicators, the use stage dominates the overall results for the start-stop and micro-hybrid application. For the conventional ICE, the manufacturing stage is dominant for LFP and for PbB both manufacturing and use stage are in the same magnitude. As described in section 3.3, the use stage refers to fuel saving due to the battery technology on car level, independent of the battery chemistry. In the case of PbB the weight difference compared to LFP batteries has also been considered.

In Figure 4-3 the overall results per battery technology and vehicle application according to the functional unit is displayed.


Figure 4-3: Overall Life Cycle GWP per battery technology, vehicle application and FU

In Figure 4-4 the main contributors to the manufacturing stage are displayed.

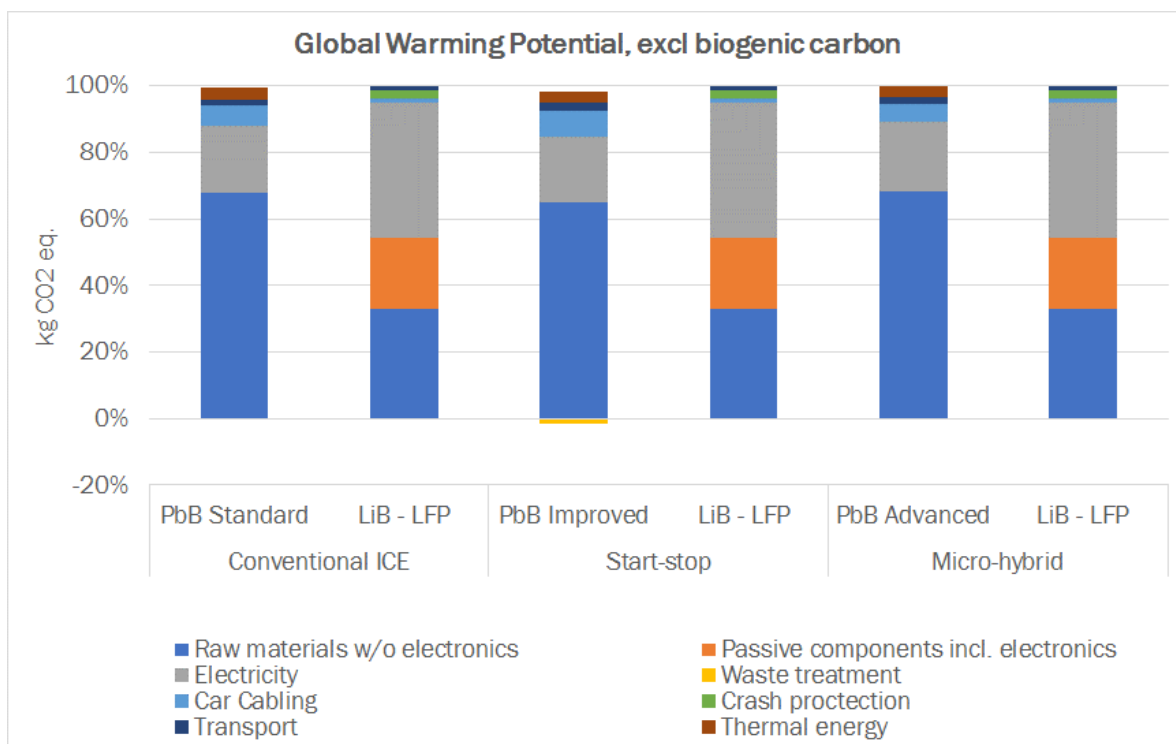


Figure 4-4: Main contributors to the GWP (manufacturing stage) per battery technology, vehicle application and FU

For PbB the manufacturing stage is dominated by the raw materials (approx. 65%) followed by electricity (approx. 20%). In the case of LiB - LFP, the electricity dominates the manufacturing stage (approx. 40%) followed by the raw materials production (approx. 35%) and the passive components including electronics (approx. 20%). Other components such as car cabling (approx. 5% for PbB and 1% for LiB - LFP) and crash protection (3% for LiB - LFP) have a lower contribution to the manufacturing stage results.

4.4. Acidification Potential

The acidification of soils and waters occurs predominantly through the transformation of air pollutants into acids. This leads to a decrease in the pH-value of rainwater and fog from 5.6 to 4 and below. Sulphur dioxide and nitrogen oxide and their respective acids (H_2SO_4 und HNO_3) produce relevant contributions. This damages ecosystems, whereby forest dieback is the most well-known impact.

Acidification has direct and indirect damaging effects (such as nutrients being washed out of soils or an increased solubility of metals into soils). But even buildings and building materials can be damaged. Examples include metals and calcium carbonate-based rocks (e. g. marble, limestone), which are corroded or disintegrated at an increased rate.

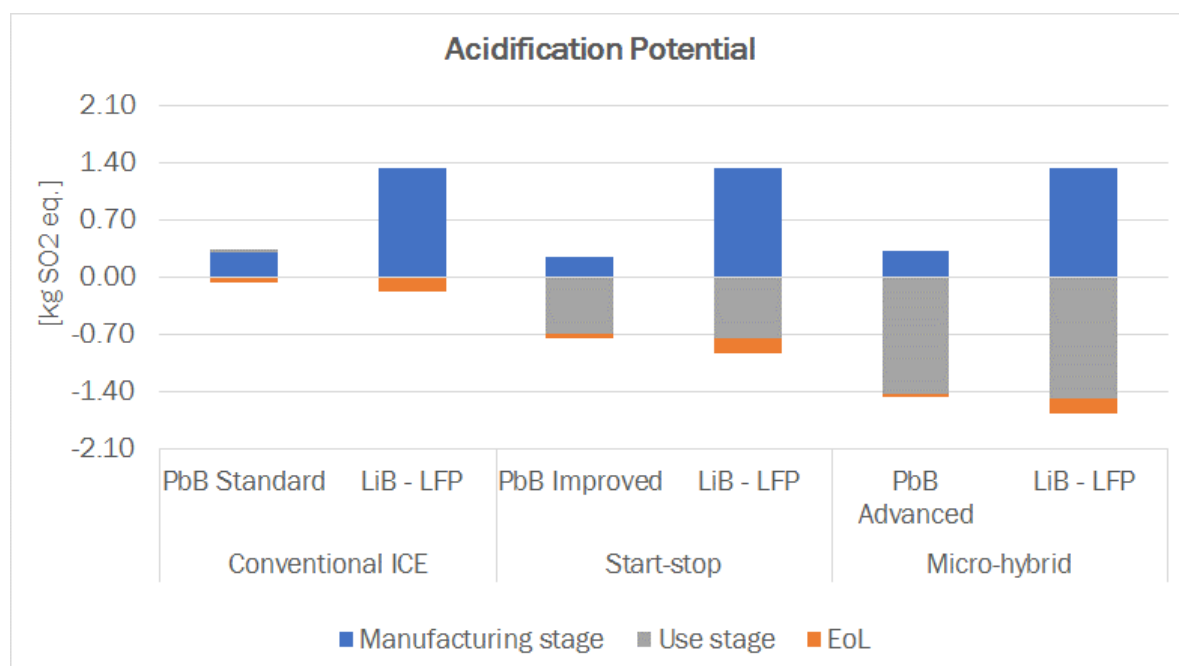
In Table 4-4 the AP for the lead and LFP batteries according to the different technologies and vehicle application for each life cycle stage is displayed.

Table 4-4: Acidification Potential [kg SO₂ eq.]

	Conventional ICE		Start-stop		Micro-hybrid	
Life Cycle Stage	PbB	LiB - LFP	PbB	LiB - LFP	PbB	LiB - LFP
Manufacturing stage	0.31	1.33	0.24	1.33	0.32	1.33
Use stage	0.03	0	-0.70	-0.75	-1.44	-1.49
EoL	-0.06	-0.18	-0.05	-0.18	-0.04	-0.18
Total Life Cycle	0.27	1.15	-0.51	0.403	-1.16	-0.34

As in the rest of analysed impact categories and indicators, the use stage dominates the overall results for the start-stop (PbB) and micro-hybrid (PbB and LiB - LFP) application. For the conventional ICE (PbB and LiB - LFP) and start-stop (LiB - LFP), the manufacturing stage is dominant. As described in section 3.3, the use stage refers to the fuel saving due to the battery technology on car level, independent of the battery chemistry. In the case of PbB the weight difference compared to LFP batteries has also been considered.

In Figure 4-5 the overall results per battery technology and vehicle application according to the functional unit is displayed.


Figure 4-5: Overall Life Cycle AP per battery technology, vehicle application and FU

In Figure 4-6 the main contributors to the manufacturing stage are displayed.

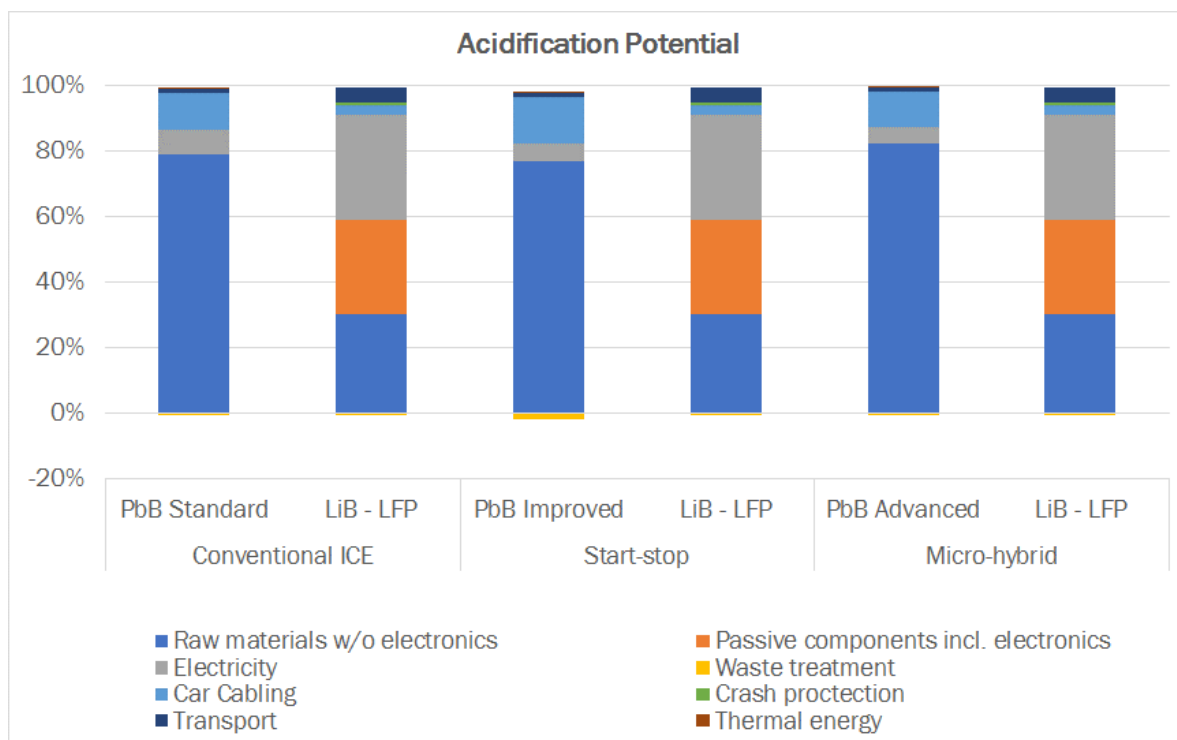


Figure 4-6: Main contributors to the AP (manufacturing stage) per battery technology, vehicle application and FU

For all battery types the manufacturing stage is dominated by the raw materials (approx. 80% - PbB and 30% - LFP) followed by electricity (approx. 6% for PbB and 30% LiB - LFP). In the case of LFP the electricity is followed by the passive components including electronics (approx. 30%). Other components such as; car cabling (approx. 10% PbB and 3% LiB - LFP) and crash protection (1% for LiB - LFP) have a lower contribution to the manufacturing stage results.

4.5. Eutrophication Potential

Eutrophication is the enrichment of nutrients in the environment. Eutrophication can be aquatic or terrestrial. Air pollutants, wastewater and fertilization in agriculture all contribute to eutrophication.

The result in water is an accelerated algae growth, which in turn, prevents sunlight from reaching the lower depths. This leads to a decrease in photosynthesis and less oxygen production. In addition, oxygen is needed for the decomposition of dead algae. Both effects cause a decreased oxygen concentration in the water, which can eventually lead to fish dying and to anaerobic decomposition (decomposition without the presence of oxygen). Hydrogen sulphide and methane are thereby produced, further damaging the ecosystem.

Overly nutrient enriched soils may result in an increased susceptibility of plants to diseases and pests as well as degradation of plant stability. If the nutrification level exceeds the amounts of nitrogen necessary for a maximum harvest, it can lead to an enrichment of nitrate. This can cause, by means of leaching, increased nitrate content in groundwater and may also end up in drinking water. Nitrate at low levels is harmless from a toxicological point of view. However, nitrite, a reaction product of nitrate, is toxic to humans.

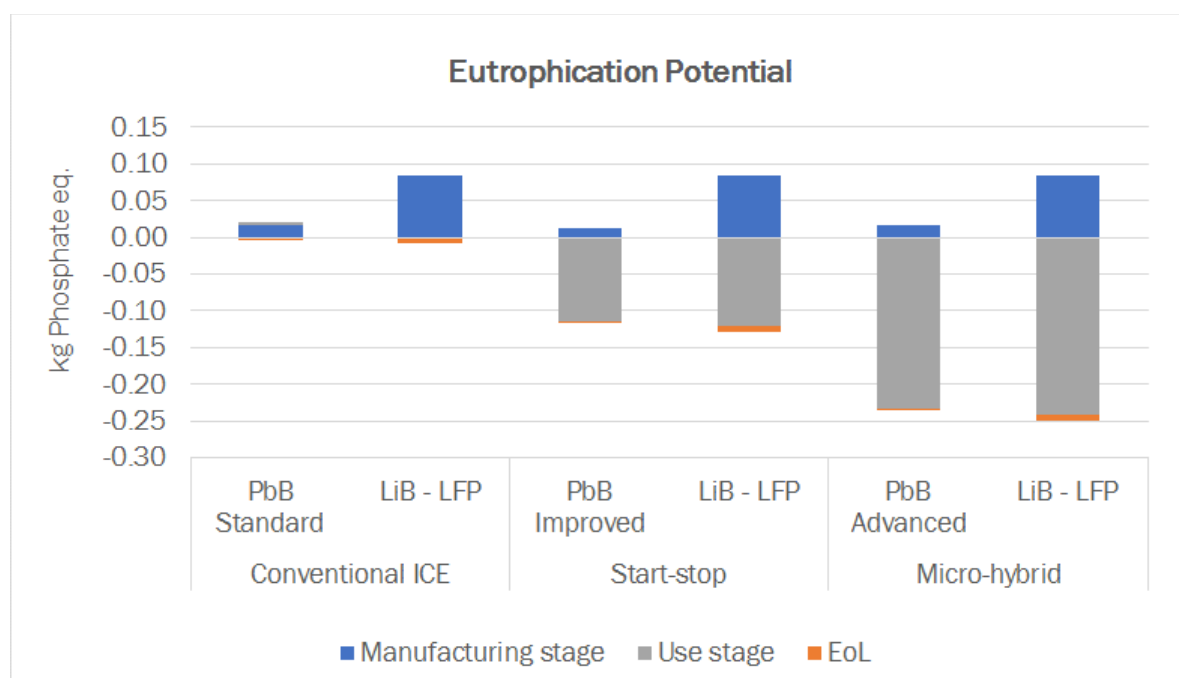
In Table 4-5 the EP for the lead and LFP batteries according to the different technologies, vehicle application and FU for each life cycle stage is displayed.

Table 4-5: Eutrophication Potential (EP) [kg Phosphate eq.]

Life Cycle Stage	Conventional ICE		Start-stop		Micro-hybrid	
	PbB	LiB - LFP	PbB	LiB - LFP	PbB	LiB - LFP
Manufacturing stage	0.02	0.08	0.01	0.08	0.02	0.08
Use stage	0.01	0	-0.11	-0.12	-0.23	-0.24
EoL	-0.005	-0.01	-0.002	-0.01	-0.001	-0.01
Total Life Cycle	0.02	0.08	-0.10	-0.04	-0.22	-0.16

As in almost all of analysed impact categories and indicators, the use stage dominates the overall results for the start-stop and micro-hybrid application. For the conventional ICE, the manufacturing stage is dominant for LiB - LFP and PbB. As described in section 3.3, the use stage refers to the fuel saving due to the battery technology on car level, independent of the battery chemistry. In the case of PbB the weight difference compared to LFP batteries has also been considered.

In Figure 4-7 the overall results per battery technology and vehicle application according to the functional unit is displayed.


Figure 4-7: Overall Life Cycle EP per battery technology, vehicle application and FU

In Figure 4-8 the main contributors to the manufacturing stage are displayed.

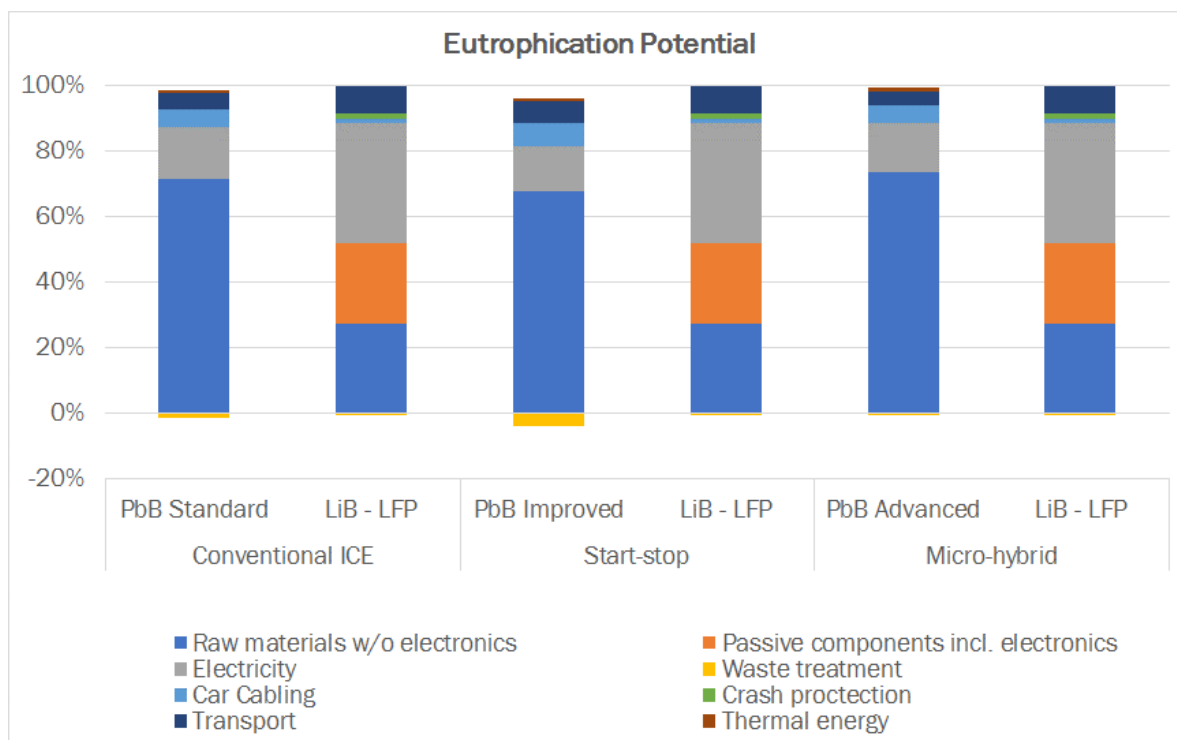


Figure 4-8: Main contributors to the EP (manufacturing stage) per battery technology, vehicle application and FU

For PbB the manufacturing stage is dominated by the raw materials (approx. 74%) followed by electricity (approx. 15%). In the case of LiB – LFP, the electricity consumption dominates the manufacturing stage (approx. 35%) followed by the raw materials (approx. 30%) and the passive components including electronics (approx. 25%). Other components such as; car cabling (approx. 5% for PbB and 1% for LiB - LFP) and crash protection (2% for LiB - LFP) have a lower contribution to the manufacturing stage results.

4.6. Photochemical Ozone Creation Potential

Despite playing a protective role in the stratosphere, at ground-level ozone is classified as a damaging trace gas. Photochemical ozone production in the troposphere, also known as summer smog, is suspected to damage vegetation and material. High concentrations of ozone are toxic to humans.

In the presence of nitrogen oxides and hydrocarbons (e. g. VOCs), ultraviolet radiation from the sun drives complex chemical reactions, producing aggressive reaction products, one of which is ozone. Nitrogen oxides alone do not cause high ozone concentration levels.

Hydrocarbon emissions occur from incomplete combustion, in conjunction with petrol (storage, turnover, refuelling etc.) or from solvents. High concentrations of ozone arise when the temperature is high, humidity is low, when air is relatively static and when there are high concentrations of hydrocarbons. Today it is thought that the presence of nitrogen monoxide (NO) and carbon monoxide (CO) reduces the accumulated ozone to NO₂, CO₂ and O₂. Surprisingly, this means, that high concentrations of ozone may not necessarily occur near hydrocarbon emission sources but can occur in less polluted areas.

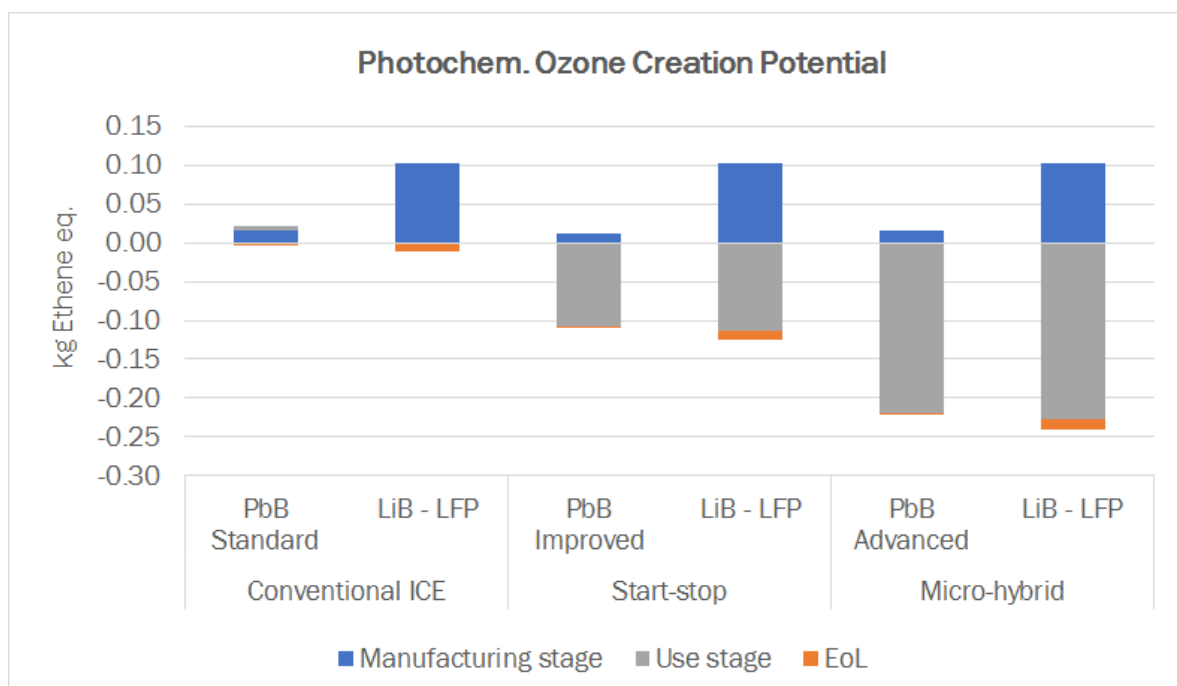
In Table 4-6 the POCP for the lead and LFP batteries according to the different technologies, vehicle application and FU for each life cycle stage is displayed.

Table 4-6: Photochemical Ozone Creation Potential (POCP) [kg Ethene eq.]

	Conventional ICE		Start-stop		Micro-hybrid	
Life Cycle Stage	PbB	LiB - LFP	PbB	LiB - LFP	PbB	LiB - LFP
Manufacturing stage	0.02	0.10	0.01	0.10	0.02	0.10
Use stage	0.005	0	-0.11	-0.11	-0.22	-0.23
EoL	-0.003	-0.01	-0.002	-0.01	-0.002	-0.01
Total Life Cycle	0.02	0.09	-0.10	-0.02	-0.21	-0.14

As in the rest of analysed impact categories and indicators, the use stage dominates the overall results for the start-stop and micro-hybrid application. For the conventional ICE, the manufacturing stage is dominant. As described in section 3.3, the use stage refers to the fuel saving due to the battery technology on car level, independent of the battery chemistry. In the case of PbB the weight difference compared to LFP batteries has also been considered.

In Figure 4-9 the overall results per battery technology and vehicle application according to the functional unit is displayed.


Figure 4-9: Overall Life Cycle POCP per battery technology, vehicle application and FU

In Figure 4-10 the main contributors to the manufacturing stage are displayed.

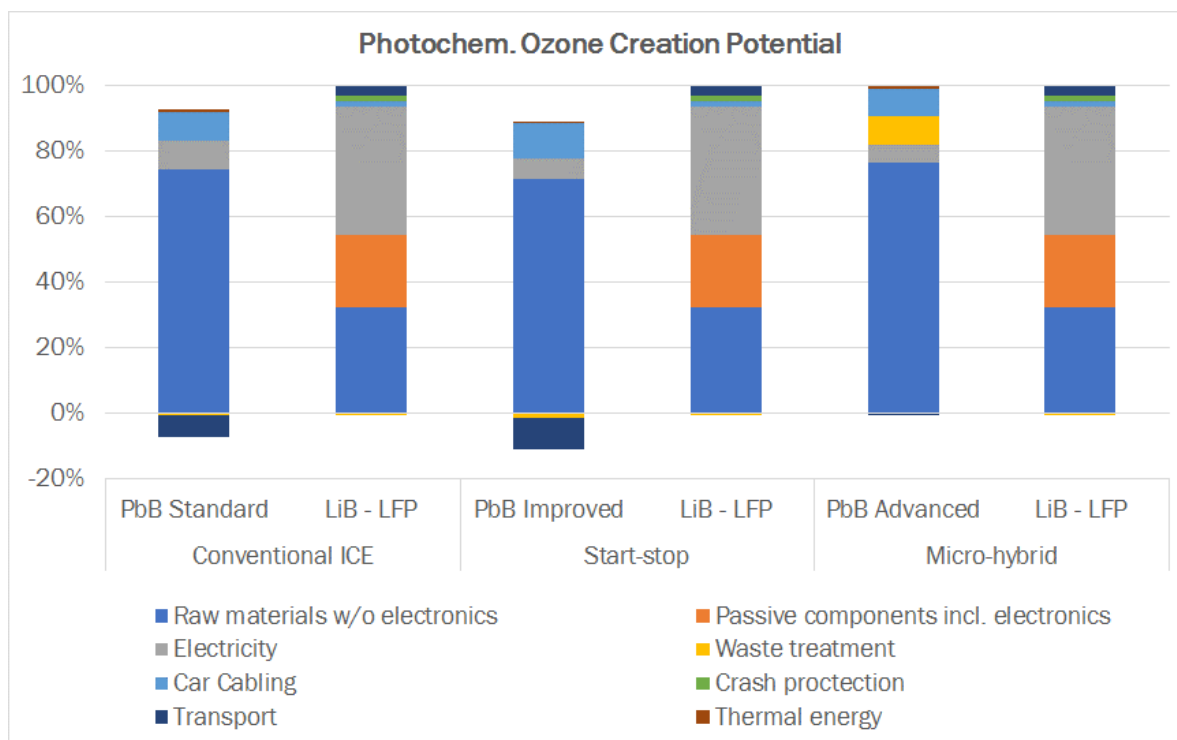


Figure 4-10: Main contributors to the POCP (manufacturing stage) per battery technology, vehicle application and FU

For PbB the manufacturing stage is dominated by the raw materials (approx. 85%) followed by electricity (approx. 8%). In the case of LiB - LFP, the electricity dominates the manufacturing stage (approx. 40%), followed by the raw materials (approx. 30%) and the passive components including electronics (approx. 20%). Other components such as; car cabling (approx. 10% for PbB and 2% for LiB - LFP) and crash protection (2% for LiB - LFP) have a lower contribution to the manufacturing stage results.

5. Interpretation

5.1. Identification of Relevant Findings

The batteries assessed in this study are required in conventional, start-stop and micro-hybrid vehicles. Based on the assumptions defined for the study, the use stage dominates the overall life cycle for all battery types (Pb and LFP) for start-stop and micro-hybrid due to the fuel saving properties. The lead batteries have a higher weight compared to the LFP batteries, which leads to an increase in fuel consumption. This effect is especially visible for the conventional ICE vehicles using standard vs LFP batteries.

In the manufacturing stage, for PbB, lead production and electricity use are most often the primary drivers of impacts. Raw materials like sulfuric acid and plastic parts can also have a noticeable contribution. For LFP batteries, electricity, cell raw materials and passive components with electronics have a higher contribution to the manufacturing stage, while the crash protection and car cabling have minor contribution to all impact categories analysed.

In the EoL, the collection rate is 97.3% for all battery types and applications (based on an analysis of collection rates seen for automotive lead batteries in the EU). After disassembly, the substitution approach has been applied for PbB where these batteries are recycled in the production of secondary lead on the input side of the production stage. For LFP batteries parts have been disassembled and treated separately having the cells sent to incineration with energy recovery and all other materials; battery case, cabling and electronics send to material recovery with the application of credits accordingly.

Table 5-1 presents a summary of the largest drivers of results. Further details can be found in the sections above.

Table 5-1: Summary of results main contributors for all battery types, vehicle applications and FU in percentage

Impact category	Main LC contributing to overall results	Main contributor to manufacturing results	Main input/output contributing to overall results
PED	<u>PbB</u> Use stage: 40% (conventional) 95% (Start-stop) 97% (micro hybrid) Manufacturing: 53% (conventional) <u>LiB - LFP</u> Use stage: 77% (Start-stop) 87% (micro hybrid) Manufacturing: 91% (conventional)	<u>PbB</u> Raw materials without electronics 60% / Electricity 28% <u>LiB - LFP</u> Raw materials without electronics 42% / Electricity 33% / Passive components with electronics 22%	<u>PbB</u> Non-renewable energy resources 84 - 96% <u>LiB - LFP</u> Non-renewable energy resources 96 - 98%

GWP	<u>PbB</u> Use stage: 46% (conventional) 96% (Start-stop) 98% (micro hybrid) Manufacturing: 47% (conventional) <u>LiB - LFP</u> Use stage: 80% (Start-stop) 89% (micro hybrid) Manufacturing: 96% (conventional)	<u>PbB</u> Raw materials without electronics 68% / Electricity 20% <u>LiB - LFP</u> Electricity 41% / Raw materials without electronics 33% / Passive components with electronics 22%	<u>PbB</u> Carbon dioxide emission to air 94 - 99% <u>LiB - LFP</u> Carbon dioxide emission to air 88 - 99%
AP	<u>PbB</u> Use stage: 71% (Start-stop) 57% (micro hybrid) Manufacturing: 76% (conventional) <u>LiB - LFP</u> Use stage: 33% (Start-stop) 50% (micro hybrid) Manufacturing: 88% (conventional) 59% (Start-stop) 44% (micro hybrid)	<u>PbB</u> Raw materials without electronics 80% / Electricity 7% <u>LiB - LFP</u> Electricity 32% / Raw materials without electronics 31% / Passive components with electronics 29%	<u>PbB</u> Sulphur dioxide emission to air 65 - 83% <u>LiB - LFP</u> Sulphur dioxide emission to air 68 - 76%
EP	<u>PbB</u> Use stage: 95% (Start-stop) 93% (micro hybrid) Manufacturing: 62% (conventional) <u>LiB - LFP</u> Use stage: 57% (Start-stop) 72% (micro hybrid) Manufacturing: 92% (conventional) 40% (Start-stop)	<u>PbB</u> Raw materials without electronics 73% / Electricity 15% <u>LiB - LFP</u> Electricity 37% / Raw materials without electronics 28% / Passive components with electronics 25%	<u>PbB</u> Emission to fresh water 44 - 87% <u>LiB - LFP</u> Emissions to fresh water 12 - 86%
POCP	<u>PbB</u> Use stage: 89% (Start-stop) 93% (micro hybrid) Manufacturing:	<u>PbB</u> Raw materials without electronics 85% / Electricity 8% <u>LiB - LFP</u>	<u>PbB</u> Organic emissions to air 33 - 73% <u>LiB - LFP</u>

68% (conventional) <u>LiB - LFP</u> Use stage: 50% (Start-stop) 66% (micro hybrid) Manufacturing: 90% (conventional) 45% (Start-stop)	Electricity 40% / Raw materials without electronics 33% / Passive components with electronics 22%	Organic emissions to air 32 - 99%
--	---	--------------------------------------

5.2. Assumptions and Limitations

The main limitation between the data used for both batteries types has to do with the data origin, lead-based battery data are an industry average while LFP is literature based but validated by several experts from the battery and automotive sector. (see section 3.1.2).

To cover the data gap of waste generation during manufacturing LFP batteries, the waste treatment assuming a weight increase of 5% of all cell components mass amounts and 3% for passive components and electronics (except car cabling and crash protection) has been included in the model and results. This approach has been taken from the PEFCR of rechargeable batteries²¹. The same reference has been taken to include the manufacturing electricity, water, auxiliary materials and emissions.

The net reduction in fuel consumption is a result of the application engine technology, of which the battery forms an integral part. The fuel savings presented, in Table 2-1, represent a best case assumption for the battery as the benefit is not exclusively due to the merit of the batteries, but the batteries do enable this engine technology use.

The emission profile of the vehicle from the combustion of the gasoline only considers the contribution of the CO₂ to the GWP and SO₂ to the AP. While other contributing emissions might exist, CO₂ and SO₂ are predominant and hence provides a representative picture of the contribution of the burning of fuel in the engine to the GWP and AP stemming from use of the vehicle.

At the EoL stage a collection rate of 97.3% has been applied for LFP and lead-based batteries. While all old lead batteries on the market are taken back and recycled by manufacturers, there is an small amount which have been assumed to be untreated, accounting for any batteries not received after being used (due to the 'hoarding effect', etc.).

Uncertainties associated with the assumptions on the weight of LFP battery, vehicle lifetime, fuel saving for start-stop and micro-hybrid have been assessed via the sensitivity analysis in the sections below.

5.3. Sensitivity Analysis Results

Sensitivity analyses were performed to test the variation of the results towards changes in parameter values that are based on assumptions or otherwise uncertain. Global warming potential has been selected for the analysis of this results.

²¹ Page 72: https://ec.europa.eu/environment/eussd/smgp/pdf/PEFCR_Batteries.pdf

5.3.1. LFP battery weight reduction

As LFP batteries may have the potential of a lower weight a variation of the weight of the battery from 12 kg to 10 kg has been assessed. The reduction of the weight has been done by reducing the amount of battery components equally and proportionally to match the 10 kg weight in the manufacturing and EoL stages. As in the base scenario, this weight includes the electronics and excludes the crash protection and car cabling which remain the same regardless of this variation. The use stage remains the same as the data used is not linked to the battery weight rather the fuel saving according to the vehicle technology and battery specifications.

Table 5-2: Battery reference flows per Functional Unit (LFP battery weight reduction)

Battery application	Li-ion battery type	Weight (kg) baseline	Weight (kg) scenario	Capacity (Ah)	Lifetime (years)	No. of batteries vehicle lifetime
Conventional ICE	LFP	12	10	60	8	1.25
Start-stop	LFP	12	10	60	8	1.25
Micro-hybrid	LFP	12	10	60	8	1.25

Table 5-3: Global Warming Potential [kg CO₂ eq.] – LFP weight sensitivity

Total LC GWP (kg CO ₂ eq.) results per FU - sensitivity analysis				
Application	Battery type	Weight (12 kg) baseline	Weight (10 kg) scenario	Variation (%)
Conventional ICE	LiB – LFP	243	201	17%
Start-Stop	LiB – LFP	-788	-829	5%
Micro-hybrid	LiB – LFP	-1818	-1858	2%

The results in Table 5-3 above and Figure 5-1 show that the reduction of the LFP battery weight would cause a reduction of the environmental profile for conventional vehicles (lower by 17%) due to the consumption of less materials and therefore also of waste treatment in the EoL. For start-stop and micro-hybrid applications the negative values increase in the same magnitude and results in a variation of 2 to 5%.

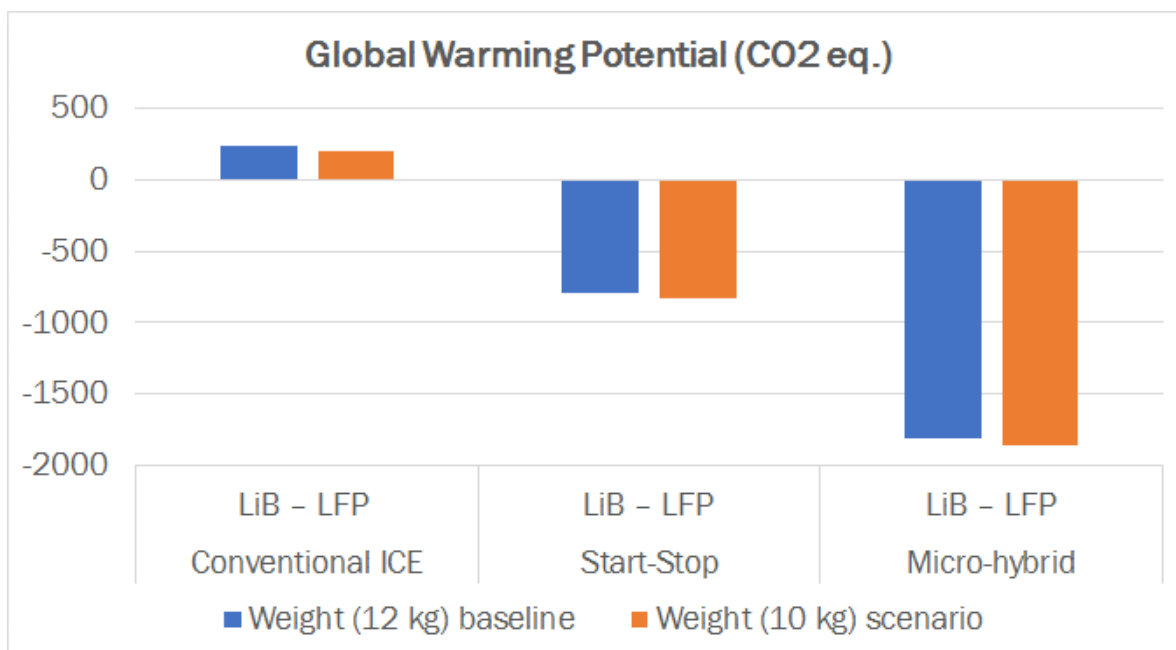


Figure 5-1: Sensitivity analysis – total GWP – LFP battery weight reduction

5.3.2. LFP battery lifetime increase

A variation of the LFP battery lifetime increase (from 8 years to 10 years and 15 years) has been assessed. The lifetime has a direct influence on the reference flow (number of batteries with electronics) required to fulfil the function of the vehicle lifetime (10-year, 150,000 km).

Table 5-4: Battery reference flows per Functional Unit (LFP battery lifetime increase)

Battery application	Li-ion battery type	No. of batteries vehicle lifetime baseline (8 yr. battery)	No. of batteries vehicle lifetime scenario A (10 yr. battery)	No. of batteries vehicle lifetime scenario B (15 yr. battery)
Conventional ICE	LFP	1.25	1	0.67
Start-stop	LFP	1.25	1	0.67
Micro-hybrid	LFP	1.25	1	0.67


Table 5-5: Global Warming Potential [kg CO₂ eq.] – LFP lifetime sensitivity – scenario A

Total LC GWP (kg CO ₂ eq.) results per FU - sensitivity analysis				
Application	Battery type	Lifetime (8 yr.) baseline	Lifetime (10 yr.) scenario	Variation to baseline (%)
Conventional ICE	LiB – LFP	243	194	20%
Start-Stop	LiB – LFP	-788	-835	6%
Micro-hybrid	LiB – LFP	-1818	-1865	3%

Table 5-6: Global Warming Potential [kg CO₂ eq.] – LFP lifetime sensitivity – scenario B

Total LC GWP (kg CO ₂ eq.) results per FU - sensitivity analysis				
Application	Battery type	Lifetime (baseline 8 y)	Lifetime (15 y) scenario B	Variation to baseline (%)
Conventional ICE	LiB – LFP	243	131	46%
Start-Stop	LiB – LFP	-788	-899	14%
Micro-hybrid	LiB – LFP	-1818	-1929	6%

The results in Table 5-5, Table 5-6 and Figure 5-2 below show that a higher lifetime for the LFP batteries would benefit its profile gradually as less batteries are needed to fulfil the service life of the application.

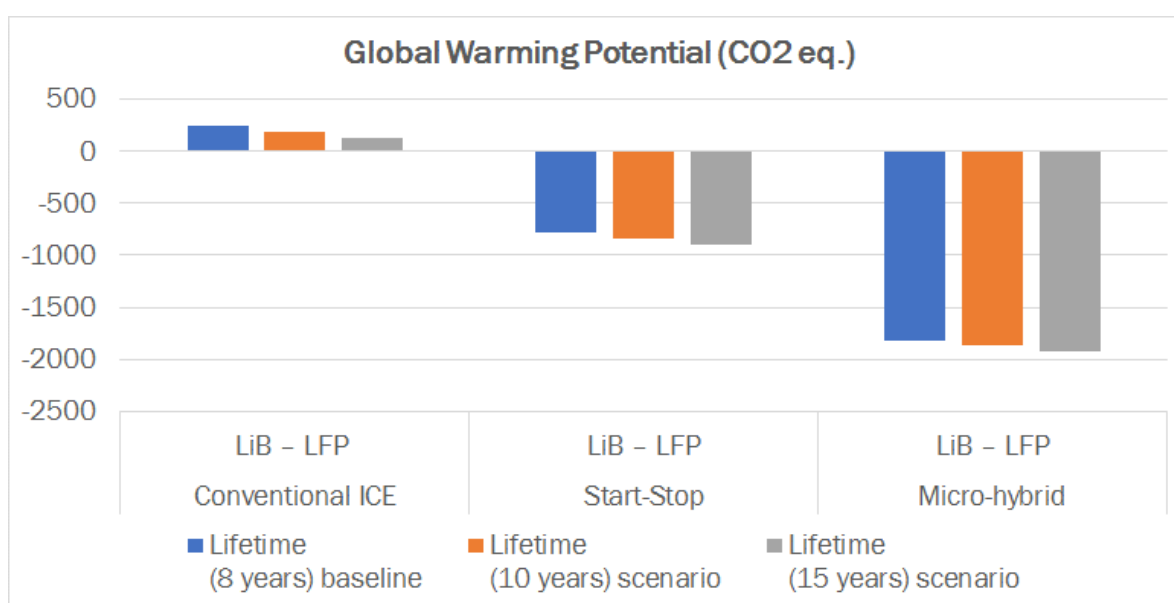
Figure 5-2: Sensitivity analysis – total GWP – LFP battery lifetime increase

5.3.3. Energy/fuel savings increase for LiB - LFP

In the use stage, it has been assumed that same energy/fuel savings apply for PbB and LiB - LFP in start-stop and micro-hybrid application. As LiB - LFP may have an additional saving potential, an assumption has been made and tested 1% benefit²² for LiB – LFP (see Table 5-7) vs PbB (see Table 4-3).

Table 5-7: Global Warming Potential [kg CO₂ eq.] –1% fuel savings sensitivity

Life Cycle Stage	Start-Stop			Micro-hybrid		
	LiB – LFP baseline	LiB - LFP 1% scenario	Variation (%)	LiB – LFP baseline	LiB - LFP 1% scenario	Variation (%)
Manufacturing stage	254	254	0%	254	254	0%

²² Information provided by ACEA members.

Use stage	-1030	-1288	25%	-2060	-2318	13%
EoL	-12	-12	0%	-12	-12	0%
Total Life Cycle	-788	-1046	33%	-1818	-2075	14%

Figure 5-3 show the baseline results for PbB and LiB – LFP batteries, compared to a scenario where LFP battery would benefit from a higher energy/fuel saving in the use stage for Start-stop and Micro-Hybrid vehicle applications. The fuel saving increase of 1% would result in an overall benefit within the range of 14 to 33% for LiB – LFP batteries.

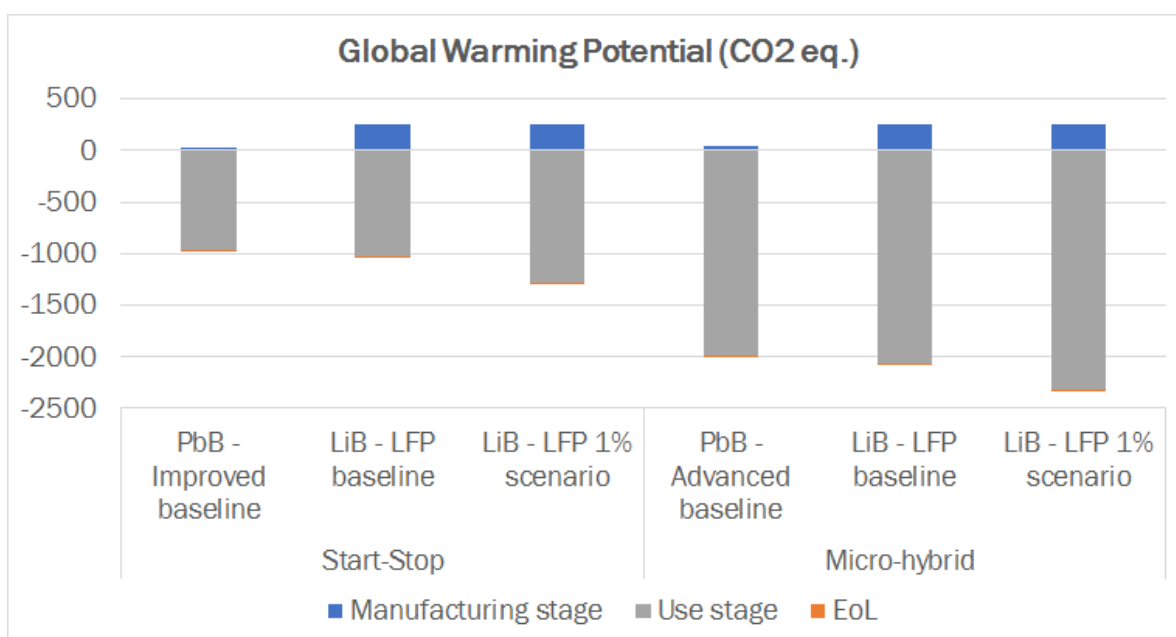


Figure 5-3: Sensitivity analysis – GWP per LC stage for PbB and LiB - LFP for Start-stop and Micro-hybrid vehicles – 1% higher fuel saving for LiB - LFP battery

5.3.4. Vehicle lifetime increase

The functional unit considers a 10-year lifetime of a vehicle with 150,000 km, a 15-year lifetime has been analysed. It has been assumed the total driving distance during the vehicle life is unchanged, although the lifetime has been increased. The table below show the number of batteries needed to fulfil this lifetime for lead-based and LFP batteries.

Table 5-8: Battery reference flows per Functional Unit (vehicle lifetime increase)

Lead battery type				Li-ion LFP battery		
Vehicle application	Lifetime years	No. of batteries vehicle lifetime (10 yr.)	No. of batteries vehicle lifetime (15 yr.)	Lifetime years	No. of batteries vehicle lifetime (10 yr.)	No. of batteries vehicle lifetime (15 yr.)
Standard / Conventional ICE	5	2	3	8	1.25	1.88

Lead battery type				Li-ion LFP battery		
Improved / Start-stop	5.5	1.82	2.72	8	1.25	1.88
Advanced / Micro-hybrid	6	1.66	2.5	8	1.25	1.88

Table 5-9: Global Warming Potential [kg CO₂ eq.] – vehicle lifetime sensitivity

Total LC GWP (kg CO ₂ eq.) results per FU - sensitivity analysis				
Application	Battery type	Vehicle lifetime 10 yr.	Vehicle lifetime 15 yr.	Variation (%)
Conventional ICE	PbB - Standard	83	101	22%
	LiB - LFP	243	363	50%
Start-Stop	PbB - Improved	-938	-919	2%
	LiB - LFP	-788	-666	15%
Micro-hybrid	PbB - Advanced	-1944	-1904	2%
	LiB - LFP	-1818	-1697	7%

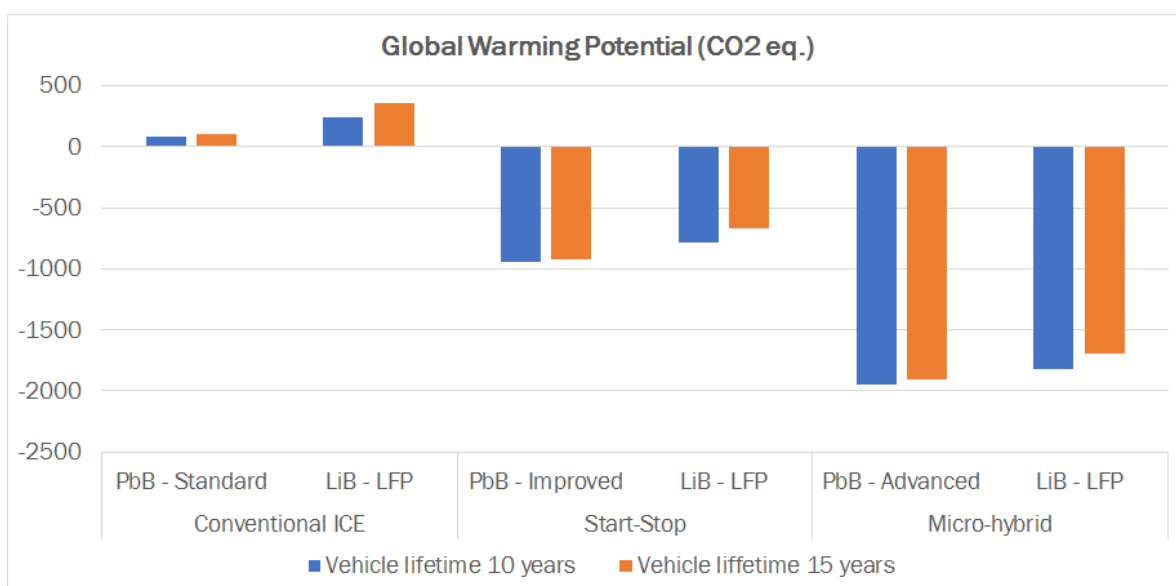


Figure 5-4: Sensitivity analysis – total GWP – vehicle lifetime increase

The results in Table 5-9 and Figure 5-4 show that for conventional vehicles, a variation of higher 50% for LiB – LFP and 22% PbB, due to the increase on the number of batteries needed to fulfil a higher vehicle lifetime. Although there is an increase on the impact for the start-stop and micro-hybrid applications during manufacturing (due to the need of more batteries), there is also an increase on EoL credits and therefore a variation on the environmental profile for all batteries.

5.3.5. EoL approach scenario

As described in section 2.4.2, there are two main EoL approaches commonly used in LCA studies to account for end of life recycling and recycled content. In Table 5-10 and Figure 5-5 the baseline

substitution approach, (also known as 0:100, closed-loop approximation, recyclability substitution or end of life approach) is compared with the cut-off approach (also known as 100:0 or recycled content approach).

Table 5-10: Global Warming Potential [kg CO₂ eq.] – EoL approach

Total GWP (CO ₂ eq.) results per FU - EoL approach scenario				
		EoL Baseline (with recovery)	EoL scenario (Cut-off)	Variation %
Conventional ICE	PbB - Standard	83	89	<10
	LiB - LFP	243	254	<10
Start-Stop	PbB - Improved	-939	-935	<1
	LiB - LFP	-788	-776	<1
Micro-hybrid	PbB - Advanced	-1944	-1942	<1
	LiB - LFP	-1818	-1806	<1

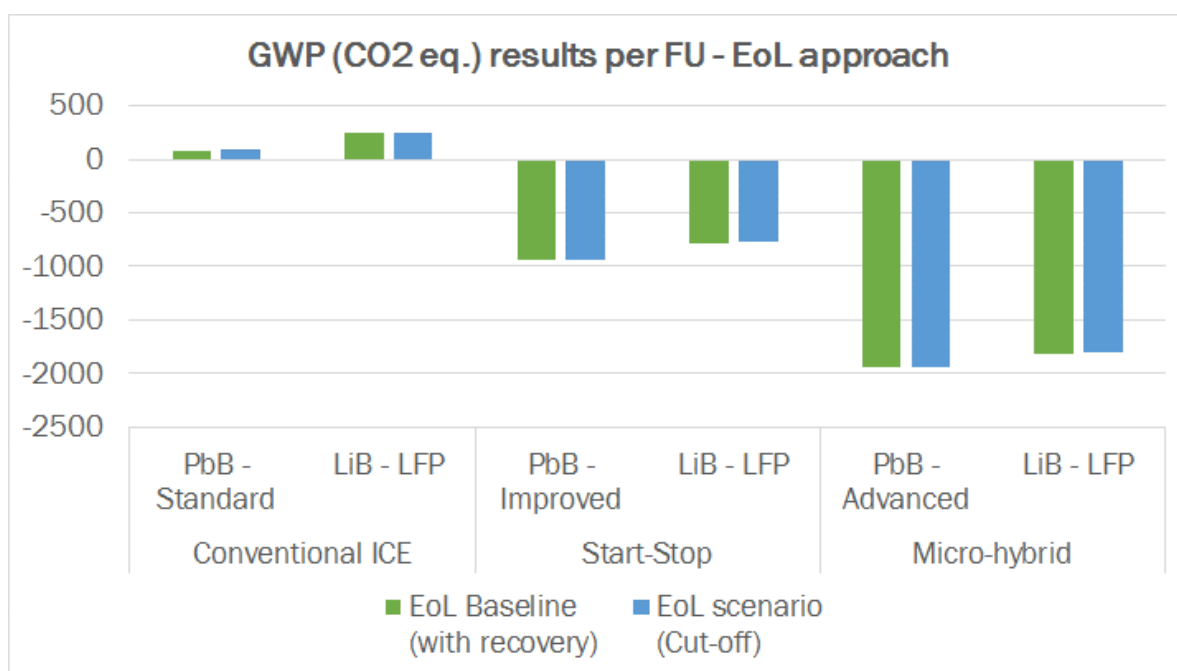


Figure 5-5: Sensitivity analysis – total GWP – EoL approach

The results in Table 5-10 and Figure 5-5 show that for conventional vehicles the variation between the two EoL approaches is lower than 5% for LiB – LFP and lower than 10% PbB. For the start-stop and micro-hybrid applications, the variation is lower than 1% for both batteries. The recovery of materials is a very important step in the EoL of product, it avoids the use of more raw materials and increases the efficiency in the use of material and energy resources avoiding disposal in landfills. This can be seen in the conventional vehicle results due to the very low contribution of the use stage to the overall results (see Figure 4-3). The defined EoL approach baseline considers the most representative of current reality available for the batteries studied.

5.4. LFP End of Life Scenario Analysis

Unlike sensitivity analyses, scenario analyses compare results between discrete sets of parameter settings or model choices. A scenario has been tested to address the potential recovery of materials from the LFP cells, currently the base scenario considers its incineration with energy recovery as no commercial material recovery is available.

As a second scenario for optimising the recycling of LFP cells Sphera worked together with Prof. Dr Markus Reuter from Helmholtz Institute in Freiberg, a metallurgist, and built up a simulation model in the HSC Sim 10 tool ²³. The software enables metallurgists or plant designers to simulate all metallurgical processes and infrastructures. It is a thermodynamic model used to identify mass streams as well as energy consumptions and losses.

The general potential recycling anticipated with existing process technology is a physical and pyrometallurgical process. In the flow chart below, we have had a second option to recover LiFePO_4 which was not considered in the baseline scenario but can be added at a later stage. The main focus in this scenario is to recover the lithium in form of lithium carbonate. The figure below shows the idealised physical crushing (under inert atmosphere) to remove the casing and then the application of pyrolysis that removes the moisture and decomposes the electrolyte (which is rather different for different battery designs and thus difficult to recycle). As a comparison, the calcined carbon rich material is split 50:50 into a pyrometallurgical route (which uses the carbon as reductant as well uses the CO in the off gas to fuel the kiln) and then processes the slag and treatment of the calcined material in the hydrometallurgical process.

The lithium rich slag will then go into the spodumene process as an example as a processing possibility. The lithium slag has a lithium content of around 6% and is treated via crushing, calcination, sulfuric acid digestion, leaching, and filtering after precipitation to produce the Li_2CO_3 . This route was chosen as an example however, in a normal recycling process, there exist various impurities in products that contaminate the final products and residues; this adds an additional purification cost to make the products and residues usable in batteries once again.

The produced waste streams are assumed to be landfilled because it was not possible to prove the economic viability of treating the waste streams to recover minor substances. As previously explained, the flowsheet maps all materials and compounds so that a good indication of where all materials flow can be obtained. This makes it possible to technologically and economically evaluate the feasibility of further processing the complex mixtures that have been highlighted in the flowsheets. A detailed simulation and engineering level study is required to determine the limitations and possibilities.

The aggregated unit process of all shown single processes in the two flow diagrams above and below are shown in the following Table 5-11.

Figure 5-6 and Figure 5-7 show the aggregated unit process of the production of the metal salt.

To summarise, the two linked flowsheets, are a part of a very large simulation model for any module from consumer electronics (220 reactors, 60 elements and all their compounds, 1000 materials, 1000 streams) and are an indication of the true recyclability of products and in this case, batteries. Note that the metal alloy produced in the furnace can be further processed in other parts of the flowsheet to produce e. g. Co, Cu and other contained valuable elements in economically viable processes.

²³ <https://www.outotec.com/products-and-services/technologies/digital-solutions/hsc-chemistry/>

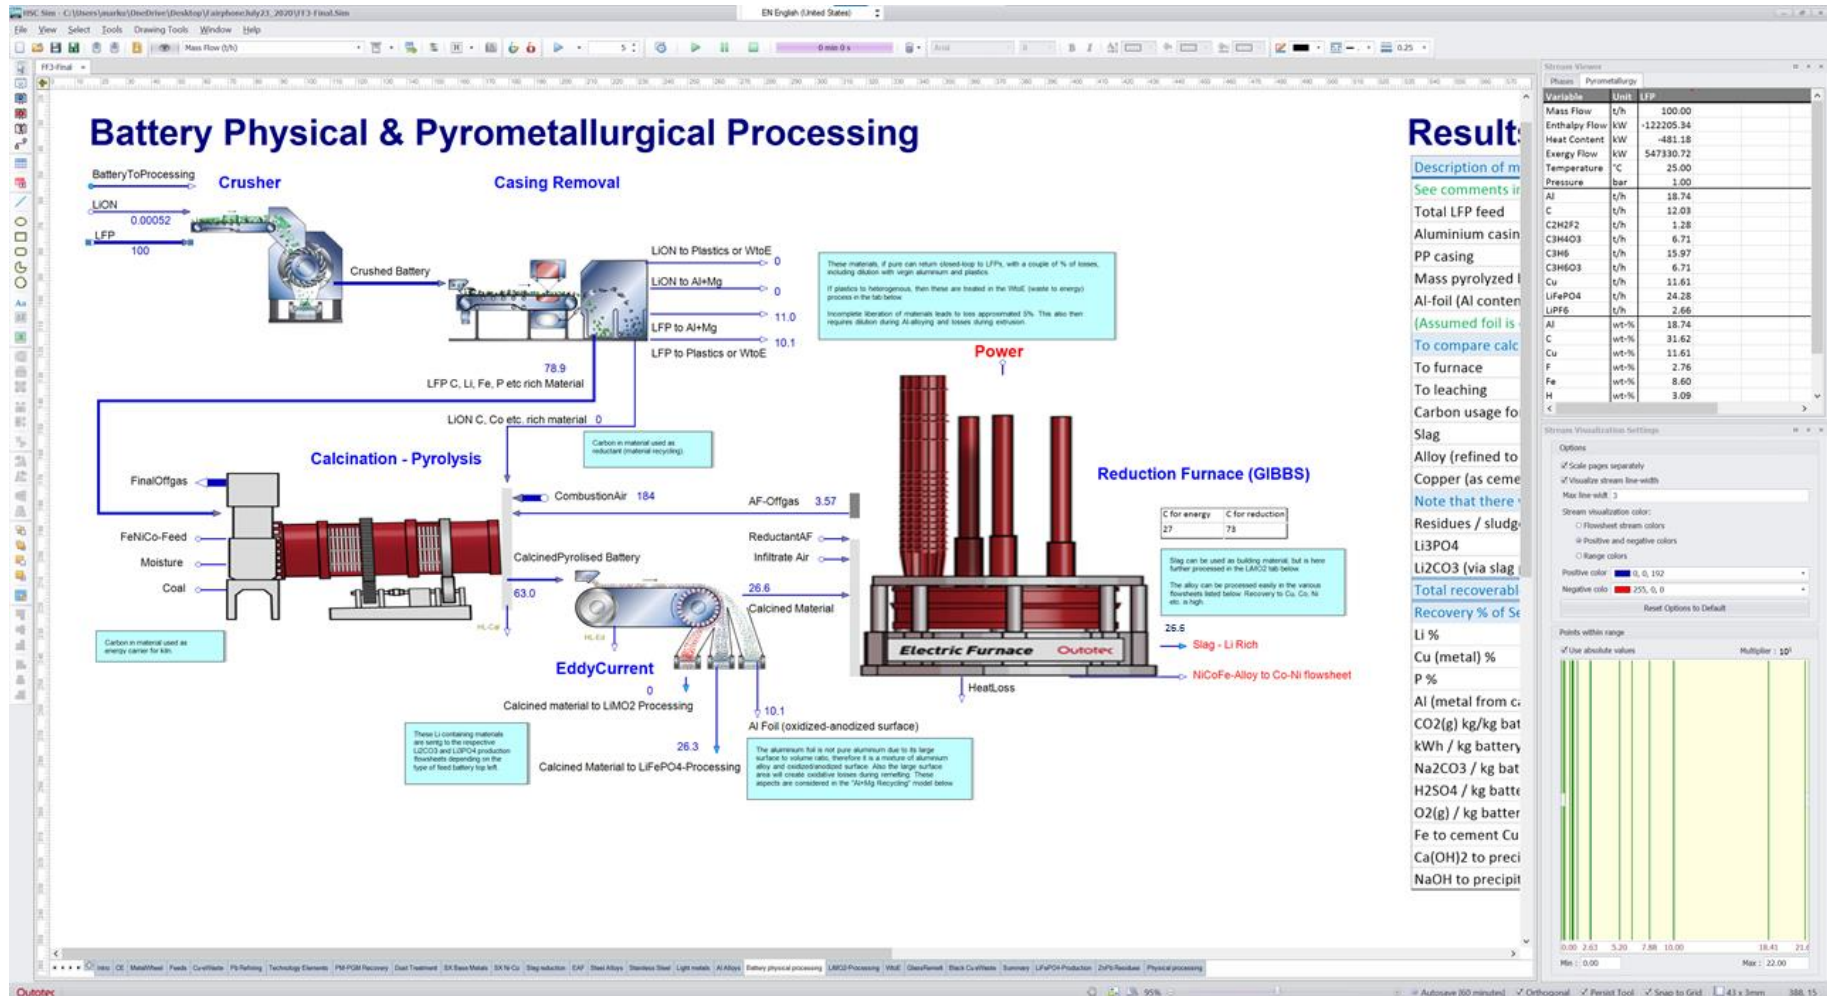


Figure 5-6: LFP Battery Physical and Pyrometallurgical Processing

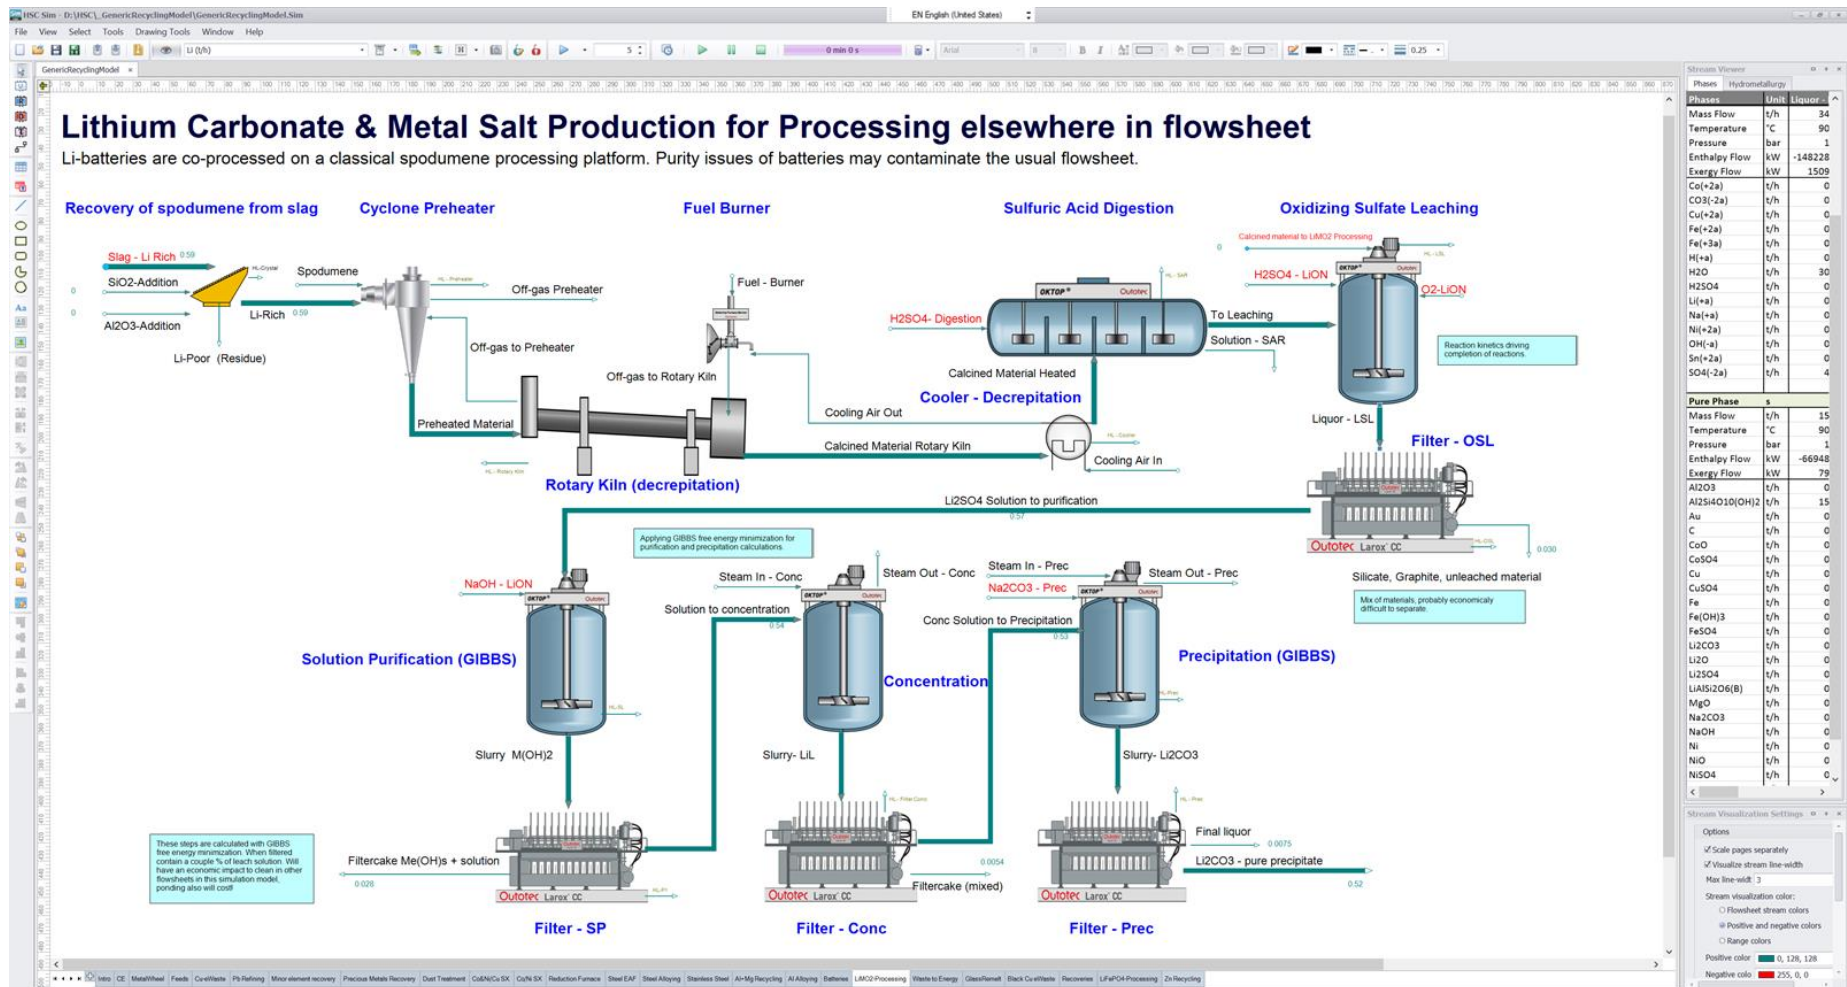


Figure 5-7: Lithium Carbonate and Metal Salt Production

Table 5-11: End of Life Cycle – LFP Battery Recovery Scenario Components Treatment

Cell / battery component	Amount	Unit	EoL Treatment	Credits
ANODE				
Copper foil	1.09	kg	copper scrap remelted	copper 99,99%
Graphite	1.01	kg	used as energy source in calcination process (see Figure 5-6).	none
CATHODE				
Al	0.67	kg	The foil is 50% oxidised and the remaining is remelted with the Al casing	credited with the most common casting alloy AlSi ₉ Cu ₃
LFP	2.28	kg	Lithium carbonate is recovered, and the waste goes to landfill	Li ₂ CO ₃ from Brine in Chile, as it has the biggest market share
Carbon black	0.12	kg	used as energy source in calcination process (see Figure 5-6).	none
Binder (PVDF)	0.12	kg		
ELECTROLYTE				
EC/DMC	1.26	kg	waste to landfill	none
LiPF ₆	0.25	kg	waste to landfill	
SEPARATOR				
PP	0.5	kg	used in reduction furnace and lands in slag which will be treated in Spodumene process	none
CELL CASE, FOIL POUCH				
Al foil	1.09	kg	recovery via remelting to cast alloy	credited with the most common casting alloy AlSi ₉ Cu ₃
BATTERY CASE				
PP	1	kg	recycling plastic granulate	virgin PP granulate

The passive components, cable and crash protection is treated as in the base scenario described in section 2.4.2 .

In the following table, the baseline scenario, which uses mainly incineration, is not as advantageous for CO₂ equivalent as the material recovery of this scenario. As described above, the main credits are given for the material recovery and the remaining waste from the hydrometallurgical filter processes (which is the smaller part) as well as slag. Only inert landfilling is considered.

Table 5-12: End of Life Cycle – LFP Battery Recovery Scenario Results

EoL stage stage / Impact Categories	Conventional ICE		Start-stop		Micro-hybrid	
	LiB – LFP baseline	LiB – LFP scenario	LiB – LFP baseline	LiB – LFP scenario	LiB – LFP baseline	LiB – LFP scenario
AP [kg SO ₂ eq.]	-0.18	-0.25	-0.18	-0.25	-0.18	-0.25
EP [kg Phosphate eq.]	-7.38E-03	0.007	-7.38E-03	0.007	-7.38E-03	0.007
GWP [kg CO ₂ eq.]	-12	-16	-12	-16	-12	-16

EoL stage stage / Impact Categories	Conventional ICE		Start-stop		Micro-hybrid	
	LiB – LFP baseline	LiB – LFP scenario	LiB – LFP baseline	LiB – LFP scenario	LiB – LFP baseline	LiB – LFP scenario
POCP [kg Ethene eq.]	-0.01	-0.01	-0.01	-0.01	-0.01	-0.01
PED [MJ]	-366	-137	-366	-137	-366	-137

The results show that the considered system boundaries are advantageous in performing material recovery, but the main mass stream is going into waste due to complexity and low value of processing back into battery grade materials. Aluminium foils are highly oxidized, i.e. there is low metal content and is hardly recoverable. Copper is best recovered as an alloy via the hydrometallurgical route because it must be leached and then recovered after purification of the electrolyte via energy intensive electrowinning. The pyrometallurgical route would make electrorefining possible, which is much more energy efficient. This study did not expand to prove economic viability of treating the waste to get materials like iron (Fe) or phosphate out of the waste stream. This is a limitation as well as a totally separate study with a higher effort than is covering the recycling of lithium carbonate.

5.5. Data Quality Assessment

Inventory data quality is judged by its precision (measured, calculated or estimated), completeness (e.g., unreported emissions), consistency (degree of uniformity of the methodology applied), and representativeness (geographical, temporal, and technological).

To cover these requirements and to ensure reliable results, first-hand industry and literature data validated by the automotive industry in combination with consistent background LCA information from the GaBi 2019 database were used. The LCI datasets from the GaBi 2019 database are widely distributed and used with the GaBi ts Software. The datasets have been used in LCA models worldwide in industrial and scientific applications in internal as well as in many critically reviewed and published studies. In the process of providing these datasets they are cross-checked with other databases and values from industry and science.

5.5.1. Precision and Completeness

- ✓ **Precision:** As most of the relevant foreground data are measured, calculated and literature based on primary information sources of the owner of the technology, precision is considered to be very good for lead-based batteries and for the LFP battery. Most background data are sourced from GaBi databases with the documented precision.
- ✓ **Completeness:** Each foreground process was checked for mass and energy balance and completeness of the emission inventory. No data were knowingly omitted. Completeness of foreground unit process data is good for lead-based batteries and good for the LFP battery. Most background data are sourced from GaBi databases with the documented completeness.

5.5.2. Consistency and Reproducibility

- ✓ **Consistency:** To ensure data consistency, all primary data were collected with the same level of detail for PbB and the most representative for LFP battery, while most background data were sourced from the GaBi databases.
- ✓ **Reproducibility:** Reproducibility is supported as much as possible through the disclosure of input-output data, dataset choices, and modelling approaches in this report. Based on this information,

any third party should be able to approximate the results of this study using the same data and modelling approaches.

5.5.3. Representativeness

- ✓ **Temporal:** All primary data were collected for the year 2017. Most secondary data come from the GaBi 2019 databases and are representative of the years 2015 - 2018. As the study intended to compare the product systems for the reference year 2018, temporal representativeness is considered to be very good.
- ✓ **Geographical:** All primary and secondary data were collected specific to the countries or regions under study. Where country-specific or region-specific data were unavailable, proxy data were used. Geographical representativeness is considered to be very good for PbB and good for LFP batteries.
- ✓ **Technological:** All primary and secondary data were modelled to be specific to the technologies or technology mixes under study. Where technology-specific data were unavailable, proxy data were used. Technological representativeness is considered to be very good for PbB and good for LFP batteries.

5.6. Model Completeness and Consistency

5.6.1. Completeness

All relevant process steps for each product system were considered and modelled to represent each specific situation. The process chain is considered sufficiently complete and detailed regarding the goal and scope of this study.

5.6.2. Consistency

All assumptions, methods and data are consistent with each other and with the study's goal and scope. Differences in background data quality were minimized by exclusively using LCI data from the GaBi 2019 databases. System boundaries, allocation rules, and impact assessment methods have been applied consistently throughout the study.

5.7. Conclusions, Limitations, and Recommendations

5.7.1. Conclusions

This study represents a comparative LCA of vehicle battery applications. Two 12 V battery chemistries have been analysed; lead-based batteries and Li-ion - LFP (lithium iron phosphate) for use in conventional, start-stop and micro-hybrid vehicles. The lead-based batteries are produced in Europe and the LFP cells are produced in China with a final battery assembly in Europe. It is assumed that all batteries are used in vehicles placed on the market in Europe and batteries at end-of-life are treated in European recycling facilities.

The lead battery data used is highly representative as it is industry data representing more than 80% of the production volume for those technologies in Europe. As for LFP batteries, no primary data were available so some inconsistencies in the data quality are inevitable. However, efforts have been made to ensure that the BoM of LFP batteries are as representative as possible. They are based on established references and the best available data validated by several automotive battery experts and automotive and battery related stakeholders.

To account for the complete life cycle, the use and EoL phases of the batteries were modelled in the study. The use phase modelling accounts for differences in battery weight and includes a best-case assumption for the associated fuel savings due to start-stop and micro hybrid applications. For the EoL lead and LFP batteries, an EoL collection rate of 97.3 % was used. For LFP batteries, two EoL scenarios were considered: the first includes the incineration of the cell (with energy generation) and recycling for electronics and passive components and the second where a recycling scenario involves recovery of the lithium in form of lithium carbonate.

Key conclusions from the study over the complete life cycle from cradle-to-grave can be summarised as such: between all batteries assessed and for most impact categories, the differences in the results are small. Given the uncertainties associated with modelling assumptions, results are not qualified as being significant; the biggest difference was obtained for the conventional vehicles. In this case, lead battery performed better in the baseline scenario due to the lower burdens in manufacturing (47%-76% depending on impact category). However, when the sensitivity of significant parameters (battery weight, lifetime, etc.) is considered, the environmental performance of LFP reaches roughly the same level as lead battery.

For both the start-stop and the micro-hybrid applications, the baseline scenario shows small differences due to large dominance of the use phase savings; these were assumed to be identical in the baseline scenario (40%-98% depending on impact category). When the sensitivity of this result is assessed by assuming a higher efficiency of the LFP batteries, they show up to a 20% better performance than lead batteries.

In the following paragraphs, the results are discussed for the individual life cycle stages.

In the manufacturing stage, the main / dominant contributor are the raw materials with around 70% of the GWP for the lead batteries and Electricity with approx. 40% followed by the raw materials with approx. 33% for the LFP batteries. Furthermore, a significant contributor to the LFP manufacturing impact is the manufacturing of the Battery Management System (BMS) that is required to ensure functional safety.

Under the baseline scenario described in Table 2-3, the environmental impact of LFP battery manufacturing is about a 6 times higher than the impact of manufacturing equivalent lead batteries.

An advantage of lead batteries is that 75% of the raw material present in the battery is recycled lead-thus reducing the environmental impact; however, LFP batteries only utilize primary materials including lithium carbonate and phosphorus as well as electronics using precious metals (which are recovered).

The use phase was addressed in this life cycle assessment by considering the differences in battery weight and by allocating the benefits of the complete start-stop and micro hybrid systems to both types of batteries. For the conventional ICE, the higher use phase emissions of lead battery are due to the higher weight which reduce the advantages in manufacturing significantly.

The EoL phase has a smaller influence on the total life cycle results (contribution of 1%-18% per impact category) than the manufacturing and use phases). Adding the potential future recycling scenario that involves recovery of the lithium in form of lithium carbonate does not significantly alter this result despite additional life cycle benefits for LFP.

Overall, the study highlights that lead battery manufacturing has a lower environmental impact compared to LiB - LFP. This benefit is maintained in the baseline scenario during the full life cycle for conventional ICE vehicles – despite the higher weight and associated use phase burdens of lead battery. The studied sensitivities of modelling parameters show that these differences may not be significant. For start-stop and micro hybrid batteries, the model shows environmental benefit for both batteries' technologies as the use stage benefits offset the manufacturing impact. In these cases, the differences found for lead battery and LiB - LFP do not appear significant.

5.7.2. Limitations and Recommendations

The results of this study are only applicable to lead and LFP batteries used in Europe for the automotive applications described. Even for this use case, the lack of primary data for LFP and the assumptions taken on battery weights, compositions and performance must be reflected in interpreting the representativity of the results.

It may not be appropriate to extrapolate these results to other regions, especially if there are significant differences in lead battery recycling rates, energy grid mixes, etc. In addition, LFP is not representative of all lithium battery chemistries and the results for other types of Li-ion batteries could be significantly different.

This study tried to isolate the contribution of the start-stop/micro-hybrid system (of which improved or advanced technology lead-based batteries are an integral part) from other technologies used to improve fuel efficiency within the vehicle i.e. base engine updates, engine downsizing, reduced roll resistance tires, vehicle weight reduction, and aerodynamic improvements. However, the total fuel consumption is influenced by all these parameters, therefore the assumed fuel reductions have some methodological limitations.

A combined scenario where all sensitivity analysis parameters are analysed together might provide a better insight on the uncertainty around LFP batteries parameters.

LFP batteries contain no economically valuable metals and thus currently have very low incentive for recycling. Typically, a mixed feed of Li ion battery chemistries is used to achieve the 50% RE target in the EU Battery Directive (2006/66/EC, DIRECTIVE, 6 September 2006). As of today, it is not economically viable to recover lithium, iron and phosphate from the cathode of the LFP battery system therefore the recycling efficiency of the LiB LFP can be estimated from maximum recyclability of other battery components, which is approximately 30%. In the future it may be possible to recover more of the LFP battery materials and as such, the study includes an LFP end-of-life scenario analysis that is described in section 5.4 that uses simulations and thermodynamic modelling to predict what is theoretically technically possible (not taking into considerations of economics).

This study shows that:

- start-stop and micro hybrid vehicles offer substantial life cycle benefits compared to conventional ICE vehicles;
- lower battery weight and greater life-span is recommended to reduce the impacts of battery manufacturing and maximise in use benefits;
- increasing material-based recycling of LFP is recommended to reduce reliance on virgin raw materials.

It is recommended to:

- Study Lithium ion battery types comprising cathode materials other than LFP;
- Study the use phase impacts of batteries more specifically; including sensitivity analysis with respect to ratio of city and highway driving, power and duration of ancillary load, etc;
- Study LiB – LFP with primary industry data rather than relying on secondary information from the available literature.
- The energy consumption amount for LiB - LFP cell manufacturing is according to the data provided in the PEFCR document (Recharge, 2018). Other literature sources show a lower energy consumption for cell manufacturing and its implications for the LCIA results should be considered in future analysis. (Qiang Dai, 2019)

References

- 2006/66/EC, DIRECTIVE. (6 September 2006). on batteries and accumulators and waste batteries and accumulators and repealing Directive 91/157/EEC. *The European Parliament and of the Council*.
- A123 Systems. (2020). 12V Starter Battery - UltraPhosphate™ Technology.
http://www.a123systems.com/wp-content/uploads/12V-Starter-Battery-Flier_2016_Gen-3.pdf.
- ACEA. (2020). Survey.
- Berger, e. a. (2020). Mineral resources in life cycle impact assessment—part I: a critical review of existing methods. *International Journal of Life Cycle Assessment*.
- BSI. (2012). *PAS 2050-1:2012: Assessment of life cycle greenhouse gas emissions from horticultural products*. London: British Standards Institute.
- Christoph Koffler, e. a. (2009). On the calculation of fuel savings through lightweight. *International Journal of LCA*.
- EPA. (2016). Proposed Determination on the Appropriateness of the Model Year 2022-2025 Light-Duty Vehicle Greenhouse Gas Emissions Standards under the Midterm Evaluation. *Technical Support Document*.
- EUROBAT. (2020). Survey on batteries weight and applications.
- G. J. May, e. a. (2018). Lead batteries for utility energy storage: A review. *Journal of Energy Storage* 15.
- Graedel, T., & Reck, B. (2015). Six Years of Criticality Assessments - What Have We Learned So Far? *Journal of Industrial Ecology*. doi:10.1111/jiec.12305
- Guinée, J. B., Gorée, M., Heijungs, R., Huppes, G., Kleijn, R., de Koning, A., . . . Huijbregts, M. (2002). *Handbook on life cycle assessment. Operational guide to the ISO standards*. Dordrecht: Kluwer.
- Hendry, S. e. (2016). Harmonization of LCA methodologies for the metal and mining industry. *International Journal of Life Cycle Assessment*.
- IHS Markit. (2019). *An Analysis of EU Collection and Recycling of Lead Based Automotive Batteries During the Period 2015-2017*.
- IPCC. (2006). *2006 IPCC Guidelines for National Greenhouse Gas Inventories - Volume 4 - Agriculture, Forestry and Other Land Use*. Geneva, Switzerland: IPCC.
- IPCC. (2013). *Climate Change 2013: The Physical Science Basis*. Geneva, Switzerland: IPCC.
- ISO. (2006). *ISO 14040: Environmental management – Life cycle assessment – Principles and framework*. Geneva: International Organization for Standardization.
- ISO. (2006). *ISO 14044: Environmental management – Life cycle assessment – Requirements and guidelines*. Geneva: International Organization for Standardization.
- JRC. (2010). *ILCD Handbook: General guide for Life Cycle Assessment – Detailed guidance*. EUR 24708 EN (1st ed.). Luxembourg: Joint Research Centre.

- Nassar, N., Barr, R., Browning, M., Diao, Z., Friedlander, E., Harper, E., . . . Graedel, T. (2012). Criticality of the Geological Copper Family. *Environmental Science & Technology*, 1071-1078.
- Pfister, S., Koehler, A., & Hellweg, S. (2009). Assessing the Environmental Impacts of Freshwater Consumption in LCA. *Environ. Sci. Technol.*, 43(11), 4098–4104.
- Qiang Dai, J. C. (2019). Life Cycle Analysis of Lithium-Ion Batteries for Automotive Applications. *Journal of battery technology and materials published quarterly online by MDPI, Batteries* 2019, 5, 48.
- Recharge. (2018). *PEFCR -Product Environmental Footprint Category Rules for High Specific Energy Rechargeable Batteries for Mobile Applications, version H*. European Commission.
- Ricardo. (2020). Lead Battery Automotive Trends Review-Final Report RD19-001611-11.
- Rohde-Brandenburger, C. K. (2009). On the calculation of fuel savings through lightweight. *Int J Life Cycle Assess* (2010) 15:128–135.
- Rohde-Brandenburger, C. K. (2009). On the calculation of fuel savings through lightweight. *International Journal of LCA*.
- Rosenbaum, R. K., Bachmann, T. M., Swirsky Gold, L., Huijbregts, M., Joliet, O., Juraske, R., . . . Hauschild, M. Z. (2008). USEtox—the UNEP-SETAC toxicity model: recommended characterisation factors for human toxicity and freshwater ecotoxicity in life cycle impact assessment. *Int J Life Cycle Assess*, 13(7), 532–546.
- Sonderegger, e. a. (2020). Mineral resources in life cycle impact assessment: part II – recommendations on application-dependent use of existing methods and on future method development needs. *International Journal of Life Cycle Assessment*.
- Sphera. (2020). GaBi Modelling Principles. http://www.gabi-software.com/fileadmin/gabi/Modelling_Principles/Modeling_Principles_-_GaBi_Databases_2020_2.pdf.
- thinkstep. (2019). *GaBi LCA Database Documentation*. Retrieved from thinkstep AG: <http://www.gabi-software.com/international/support/gabi/gabi-database-2019-lci-documentation/>
- thinkstep. (2019a). *GaBi LCA Database Documentation*. Retrieved from thinkstep AG: <http://www.gabi-software.com/international/support/gabi/gabi-database-2019-lci-documentation/>
- thinkstep. (2019b). *EU LCA LEAD Automotive Batteries - final draft*.
- van Oers, L., de Koning, A., Guinée, J. B., & Huppes, G. (2002). *Abiotic resource depletion in LCA*. The Hague: Ministry of Transport, Public Works and Water Management.
- WRI. (2011). *GHG Protocol Product Life Cycle Accounting and Reporting Standard*. Washington D.C.: World Resource Institute.

Annex A: Critical Review Statement

Critical Review Statement

COMPARATIVE LCA OF LEAD AND LFP BATTERIES FOR AUTOMOTIVE APPLICATIONS

Commissioned by: International Lead Association, United Kingdom

Prepared by: Sphera Solutions Inc., Germany

Review panel: Prof. Dr. Matthias Finkbeiner (chair), Germany
Dr. Qiang Dai, United States of America
Dr. Eberhard Meissner, Germany
Mr. Jeffrey Spangenberg, United States of America

References ISO 14040 (2006): Environmental Management - Life Cycle Assessment - Principles and Framework
ISO 14044 (2006): Environmental Management - Life Cycle Assessment – Requirements and Guidelines
ISO/TS 14071 (2014): Environmental management -Life cycle assessment - Critical review processes and reviewer competencies: Additional requirements and guidelines to ISO 14044:2006

Scope of the Critical Review

The review panel had the task to assess whether

- the methods used to carry out the LCA are consistent with the international standards ISO 14040 and ISO 14044,
- the methods used to carry out the LCA are scientifically and technically valid,
- the data used are appropriate and reasonable in relation to the goal of the study,
- the technological coverage of the industry in the prevalent LCA study is representative of current practice,
- the interpretations reflect the limitations identified and the goal of the study, and
- the study report is transparent and consistent.

The review was performed concurrently to the study according to paragraph 6.3 of ISO 14044, because the study is intended to be used for comparative assertions intended to be disclosed to the public. This review statement is only valid for this specific report in its final version 1.4 dated 05.12.2020.

Outside the scope of this review were

- the verification of assumptions made for the types and properties of batteries, vehicle systems, use cases and the recycling of batteries,
- an analysis of the LCA model and
- the verification of individual LCI datasets

Review process

The review process was coordinated between the International Lead Association (ILA), Sphera Solutions (Sphera) and the chair of the review panel. As a first step in the review process, the panel members were selected based on their specific LCA and battery competence.

After the review panel was established, a kick-off call was held on 02.07.2020. In this call, the details of the review process were agreed, and an outline of the goal and scope of the study was presented by Sphera. The first draft of the goal and scope report was submitted to the panel on the same day. The review panel provided 135 comments of general, technical and editorial nature to the commissioner by 13.07.2020. A revised goal and scope text was provided as part of the draft final report.

As a next step, the commissioner provided the first draft of the final report on 12.08.2020. The review panel provided 310 comments on the draft final report of general, technical and editorial nature and sent them to the commissioner by 28.08.2020. Sphera provided a comprehensively revised report and documentation on the implementation of the review comments on 03.11.2020. The majority of critical issues and many of recommendations of the review panel were addressed in a proper manner. A few issues needed further discussion and agreement. Therefore, a critical review panel meeting with Sphera and ILA (web conference) was held on 20.11.2020 to address the comments that needed additional information or agreement on how they are supposed to be implemented.

A revised report was sent to the panel on 30.11.2020. The panel provided a set of 28 comments. Sphera and ILA addressed them before the conclusion of the critical review process. The final version 1.4 of the report dated 05.12.2020 was provided on 05.12.2020.

The review panel acknowledges the unrestricted access to all requested information as well as the open and constructive dialogue during the critical review process. The contributions of the panel members were consistent and without any conflicting views. The comments during the process and this review statement were approved unanimously.

General evaluation

This LCA study assessed the cradle-to-grave environmental impact of a lead-based battery compared to an LFP battery for automotive application within Europe. The results of the study are to be used by the European

Automobile Manufacturers Association (ACEA), Japan Automobile Manufacturers Association (JAMA), Korea Automobile Manufacturers Association (KAMA), Association of European Automotive and Industrial Battery Manufacturers (EUROBAT), and the International Lead Association (ILA), to improve their understanding of the environmental impact of lead-based battery production from cradle-to-grave.

The study was overall performed in a professional manner using state-of-the-art methods. The study is reported in a comprehensive manner including a transparent documentation of its scope and methodological choices. Several issues were studied in sensitivity analyses.

As transparently documented in the report itself, the following aspects should be noted for a proper interpretation of the results and for potential future updates of the study:

- the representativity of the results are limited to the specific lead and LFP battery concepts defined for the use in the European automotive applications described.
- the lack of primary data for LFP and the assumptions taken on battery weights, compositions and performance must be reflected in interpreting the representativity of the results.
- the use stage benefits of the start-stop-/micro-hybrid systems depend on other technologies used to improve fuel efficiency within a vehicle, as well as the assumptions made to characterize the different vehicle systems and the vehicle operating conditions.
- the end-of-life-treatment for LFP batteries is modelled based on scenarios being representative for today, while these technologies are still evolving.

As with every LCA, the outcomes of a specific study and especially a comparative study also depend on the choices made and the data selected in the scope definition. Therefore, the results need to be interpreted in the specific context defined. Any generalization beyond the context of the defined scope, is not covered by the study as such.

Conclusion

The study has been carried out in conformity with ISO 14040 and ISO 14044 following the critical review procedures of ISO TS 14071.

07th December 2020

*Matthias
Finkbeiner*

*Qiang
Dai*

*Eberhard
Meissner*

*Jeff
Spangenberg*

(the review statement was approved by email)